



Thermal Engineering

Elixir Thermal Engg. 33 (2011) 2179-2207

Elixir
ISSN: 2229-712X

Phase change materials for solar latent heat storage applications: a review

S. Gurulingam and N. Alagumurthi

Department of Mechanical Engineering, Pondicherry Engineering College, Pondicherry – 605014, India.

ARTICLE INFO

Article history:

Received: 18 February 2011;

Received in revised form:

17 March 2011;

Accepted: 27 March 2011;

Keywords

Phase change material,
Solar energy,
Latent heat storage system,
New PCM innovations.

ABSTRACT

The use of a latent heat storage system using Phase Change Materials (PCM) is an effective way of storing thermal energy (solar energy, off-peak electricity, industrial waste heat) and has the advantages of high storage density and the isothermal nature of the storage process. In the present era the utilizations of electricity and other conventional modes are quite in effective to the present demand and in other hand the role of alternative energy resources which compensates the present energy demands of the world will be not enough for the future. Meanwhile by the year 2020 the renewable energy resources are depleting so that it will become in need of very high energy demand due to over population in India comparing to the world resources and their populations. Now it clearly shows that trapping the solar energy and storing the heat by means of suitable PCMs will give other hand support to solve the energy crisis will help to bring out a new milestone in energy storage revolutions. It has been demonstrated that, for the development of a latent heat storage system, choice of the PCM plays an important role in addition to heat transfer mechanism. The information on the latent heat storage materials and systems is enormous and published widely in the literatures. In this paper, an attempt has been made to provide information from the previous works on PCMs and latent heat storage systems. This review may have been planned to be useful to the scientists and researchers to investigate more on PCMs.

© 2011 Elixir All rights reserved.

Introduction

Scientists all over the world are in search of new and renewable energy sources to reduce the CO₂ emissions from the combustion of fossil fuels, particularly in areas where low temperature applications are involved. Solar energy has an enormous potential for the heating and cooling of buildings, producing hot water for domestic and industrial purposes, cooking, warming greenhouses for agricultural crops, etc. However, solar energy is intermittent, unpredictable, and available only during the day. Hence, its application requires efficient thermal energy storage so that the surplus heat collected during sunshine hours may be stored for later use during the night. Similar problems arise in heat recovery systems, where the waste heat availability and utilization periods are different, requiring some thermal energy storage. In thermal energy storage, the useful energy from the collector is transferred to the storage medium where it is transformed into an internal energy. This may occur in the form of latent heat, sensible heat, or both. One major drawback of sensible heat storage is the large volume required, especially when the allowable temperature swing is small. Latent heat storage is more attractive than sensible heat storage because of its high storage density with smaller temperature swing (Lane, 1983; Abhat, 1983). However, many practical problems are encountered with latent heat storage due to low thermal conductivity, variation in thermo-physical properties under extended cycles, phase segregation, sub cooling, incongruent melting, volume change and high cost. These problems have to be technically resolved before latent heat storage can be widely used.

Latent heat storage is a relatively new area of research and pioneered by Dr. Telkes in the 1940s (Lane, 1983). It did not

receive much attention, however, until the energy crisis of the late 1970s and early 1980s. PCM was first used in British trains against coolness. The first application of PCM described in the literature was their use for heating and cooling in buildings, by Telkes (1975), and Lane (1983). Telkes et al. (1978) published the idea of using PCMs in walls, better known as Trombe walls. Although research into latent heat storage for solar heating systems continues (Kaygusuz, 1999; Sari et al. 2000), it is increasingly being considered for waste heat recovery and load leveling for power generation (El-Dessouky et al. 1997).

The present paper is a compilation of much of practical information on various PCMs and latent heat storage systems. This review will help to find the suitable PCM for various purposes, suitable heat exchangers with ways to enhance the heat transfer, and it will also help to provide a variety of designs to store heat using PCMs for different applications, i.e. space heating & cooling, solar cooking, greenhouses, solar water heating and waste heat recovery systems.

Energy Storage Methods

The different forms of energy that can be stored include mechanical, electrical, and thermal energy. Mechanical energy storage systems include gravitational energy storage or Pumped Hydro Power Storage (PHPS), Compressed Air Energy Storage (CASE) and Fly- wheels. The PHPS and CAES technologies can be used for large-scale utility energy storage while flywheels are more suitable for intermediate storage. Energy storage through batteries is an option for storing the electrical energy. A battery is charged by connecting it to a source of direct electric current and when it is discharged, the stored chemical energy is converted into electrical energy. Potential applications of batteries are utility peak shaving, load leveling, and storage of electrical energy

generated by wind turbine or photovoltaic plants. The most common type of storage battery is the lead acid and Ni-Cd batteries.

Thermal energy can be stored as a change in internal energy of a material as sensible heat, latent heat, and thermo-chemical heat, or combination of these. In Sensible Heat Storage (SHS), thermal energy is stored by raising the temperature of a solid or liquid. SHS systems utilize the heat capacity and the change in temperature of the material during the process of charging and discharging. The amount of stored heat depends on the specific heat of the medium, the temperature change, and the amount of storage material.

Latent Heat Storage (LHS) is based on the heat absorption or release when a storage material undergoes a phase change from solid to liquid or liquid to gas or vice-versa. LHS systems have certain benefits in comparison with SHS systems. The most important is the higher energy density per unit mass and per unit volume.

Thermo-chemical systems rely on the energy absorbed and released in breaking and reforming molecular bonds in a completely reversible chemical reaction. In this case, the stored heat depends on the amount of storage material, the endothermic heat of reaction, and the extent of conversion.

Amongst thermal heat storage techniques, latent heat thermal energy storage is particularly attractive due to its ability to provide high energy storage density and its characteristics to store heat at constant temperature corresponding to the phase transition temperature of the PCM.

Latent heat storage can be accomplished through solid-liquid, liquid-gas, solid-gas and solid-solid phase transformations, but the only two of practical interest are the solid-liquid and solid-solid (Wang et al., 2000). Solid-gas and liquid-gas transition have a higher latent heat of fusion but their large volume changes on phase transition are associated with containment problems and rule out their potential utility in thermal storage systems. Large changes in volume make the system complex and impractical.

In solid-solid transitions, heat is stored when the material is transformed from one crystalline to another. This transition generally has smaller latent heat and volume changes than solid-liquid transition. Solid-solid PCMs offer the advantages of less rigorous container requirements and better design flexibility (Wang et al., 2000; Pillai et al., 1976). Most promising materials are organic solid solutions of pentaerythritol (melting point 188°C, latent heat of fusion 323 kJ/kg), pentaglycerine (melting point 81°C, latent heat of fusion 216 kJ/kg), Li_2SO_4 (melting point 578 °C, latent heat of fusion 214 kJ/kg) and KHF_2 (melting point 196 °C, latent heat of fusion 135kJ/kg) (Garg et al. 1985). Trombe Walls with these materials could provide better performance than a plain concrete Trombe Wall.

Solid-liquid transformations have comparatively smaller latent heat than liquid-gas. However, these transformations involve only a small change in volume (< 10 %). Solid-liquid transition has proved to be economically attractive for use in thermal energy storage systems. PCMs themselves cannot serve as a heat transfer medium. Heat transfer mediums with a heat exchanger are required to transfer energy from the source to the PCM and from PCM to the load. Therefore, Designing of the heat exchanger is an important part for improving heat transfer in latent heat storage systems. PCMs also have positive volumetric expansion on melting, so, volume design of the containers is also necessary, which should be compatible with the PCM used. Any

latent heat storage system must possess at least the following three properties: a suitable PCM with its melting point in the desired temperature range, a suitable heat exchange surface and a suitable container compatible with the PCM.

Phase Change Materials

Phase Change Materials (PCM) are latent heat storage materials. As the source temperature rises, the chemical bonds within the PCM break up as the material changes phase from solid to liquid (as is the case for solid-liquid PCMs, which are of particular interest here). The phase change is a heat-seeking (endothermic) process and therefore, the PCM absorbs heat. Upon storing heat in the storage material, the material begins to melt when the phase change temperature is reached. The temperature then stays constant until the melting process is finished.

The heat stored during the phase change process (melting process) of the material is called latent heat. Latent heat storage has two main advantages: (i) it is possible to store large amounts of heat with only small temperature changes and therefore to have a high storage density; (ii) because the change of phase at a constant temperature takes some time to complete, it becomes possible to smooth temperature variations. The comparison between latent and sensible heat storage shows that using latent heat storage, storage densities typically 5 to 10 times higher can be reached. PCM storage volume is two times smaller than that of water (Garg et al., 1985; Hasnain, 1998). Latent heat storage can be used in a wide temperature range. A large number of PCMs are known to melt with a heat of fusion in any required range. The PCM to be used in the design of thermal storage systems should accomplish desirable thermophysical, kinetics and chemical properties (Hale et al., 1971; Garg et al., 1985; Buddhi et al., 1994).

Thermo-Physical Properties

- (i) Melting temperature in the desired operating temperature range.
- (ii) High latent heat of fusion per unit volume so that the required volume of the container to store a given amount of energy is less.
- (iii) High specific heat to provide for additional significant sensible heat storage.
- (iv) High thermal conductivity of both solid and liquid phases to assist the charging and discharging of energy of the storage systems.
- (v) Small volume changes on phase transformation and small vapor pressure at operating temperatures to reduce the containment problem.
- (vi) Congruent melting of the PCM for a constant storage capacity of the material with each freezing/melting cycle.

Kinetic Properties

- (i) High nucleation rate to avoid super cooling of the liquid phase.
- (ii) High rate of crystal growth, so that the system can meet demands of heat recovery from the storage system.

Chemical Properties

- (i) Chemical stability.
- (ii) Complete reversible freeze / melt cycle.
- (iii) No degradation after a large number of freeze / melt cycles.
- (iv) Non-corrosiveness to the construction materials.
- (v) Non-toxic, non-flammable, and non-explosive materials for safety.

Moreover, low cost and large-scale availability of the PCMs is also very important.

Classification of PCMs

A classification of PCMs is given in Fig. 1. There are a large number of PCMs (organic, inorganic and eutectic), which can be identified as PCMs from the point of view melting temperature and latent heat of fusion. However, except for the melting point in the operating range, a majority of PCMs do not satisfy the criteria required for an adequate storage media as discussed in section 3.1. Organic and inorganic types of PCMs are given in Table 1 and 2 respectively. As no single material can have all the required properties for an ideal thermal storage media, one has to use the available materials and try to make up for the poor physical properties by an adequate system design. For example, metallic fins can be used to increase the thermal conductivity of PCMs, super-cooling may be suppressed by introducing a nucleating agent in the storage material, and incongruent melting can be inhibited by the use of a PCM of suitable thickness. For their very different thermal and chemical behavior, the properties of each sub-group, which affect the design of latent heat storage systems using PCMs of that sub-group, are discussed in detail below.

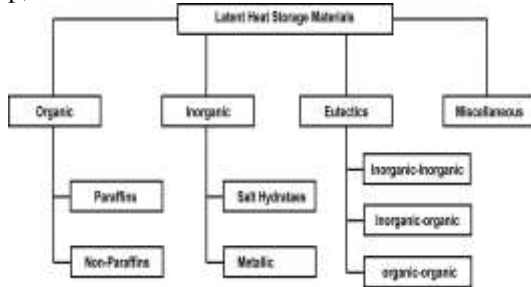


Figure 1 Classification of latent heat storage materials.

Paraffins

The normal paraffins of type C_nH_{2n+2} are a family of saturated hydrocarbons with very similar properties. Paraffins between C_5 and C_{15} are liquids, and the rest are waxy solids. Paraffin wax is the most-used commercial organic heat storage PCM (Lane, 1983; Hale et al. 1971). It consists of mainly straight chain hydrocarbons that have melting temperatures ranging from 23 to 67 °C (Abhat, 1983). Commercial-grade paraffin wax is obtained from petroleum distillation and is not a pure substance, but a combination of different hydrocarbons. In general, the longer the average length of the hydrocarbon chain, the higher the melting temperature and heat of fusion (Hiran et al., 1994). Properties of some paraffins are given in Table 3. Paraffins are easily available from many manufacturers and are usually more expensive than salt hydrates (Lane, 1983; Hale et al., 1971).

Advantages: Paraffin waxes show no tendency to segregate. They are chemically stable, although Lane (1983) reports slow oxidation when exposed to oxygen, therefore, they required closed containers. Sharma et al. (1999; 1998; 2002) report stable properties after 1500 cycles in commercial-grade paraffin wax. Paraffin wax did not show regular degradation in thermal properties after repeated melting / freezing cycles.

Paraffin waxes show high heats of fusion, as shown in Table 3. They also have no tendencies to super cool, so nucleating agents are not necessary (Lane, 1983; Buddhi et al., 1994). Paraffin waxes are safe and non-reactive (Hale et al., 1971; Hasnain, 1998). They are compatible with all metal containers and easily incorporated into heat storage systems (Lane, 1983). Care should be taken when using plastic containers as paraffins have a tendency to infiltrate and soften some plastics (Lane, 1983).

Disadvantages: Paraffins have low thermal conductivity in their solid state, as can be seen from Table 4. This presents a problem when high heat transfer rates are required during the freezing cycle. Velraj et al. (1998) reports that, this problem can be decreased using finned containers and metallic fillers, or through a combination of latent/ sensible storage systems. Aluminum honeycombs have been found to improve system performance (Hale et al., 1971). Paraffins have a high volume change between the solid and liquid stages. This causes many problems in container design (Hasnain, 1998). Lane (1983) also reports that paraffins greatly decrease heat storage capacity. Unlike Salt Hydrates, commercial paraffins generally do not have sharp, well-defined melting points. Paraffins are flammable, but this can be easily alleviated by a proper container (Hiran et al., 1994; Hale et al., 1971; Hasnain, 1998).

Hale et al., 1971; Lane, 1983; Garg et al., 1985; Buddhi, 1994; Sharma, 1999; Gustafsson et al., 1998; Zalba et al., 2003; Farid et al., 2004.

Lane, 1983; Abhat, 1983; Garg et al., 1985; Buddhi, 1994; Hale et al., 1971; Sharma, 1999.

Non-paraffins

This is the largest category of candidate materials for latent heat storage. Lane (1983; 1989), Abhat (1983) and Buddhi et al. (1994) have conducted an extensive survey of organic materials and identified a number of esters, fatty acids, alcohols, and glycols suitable for energy storage. These organic materials are further sub-groups of fatty acids and other non-paraffin organics. The non-paraffin organics are the most numerous of the PCMs, with highly varied properties. Each of these materials will have its own properties, unlike the paraffins, which have very similar properties. These materials are flammable and should not be exposed to excessively high temperature, flames or oxidizing agents. Non-paraffins are tabulated in Table 4.

Fatty Acids

Fatty acids, characterized by the chemical formula $CH_3(CH_2)_{2n}COOH$, have much the same characteristics as paraffins. Their advantage of sharper phase transformations is offset by the disadvantage of being about two or three times the cost of paraffins (Hasnain, 1998). They are mildly corrosive. Some fatty acids for low temperature latent heat storage applications are tabulated in Table 5. One promising use, given by Kauranen et al. (1991), is a system to combine fatty acids to obtain melting temperatures ranging from 20–30 °C with an accuracy of ± 0.5 °C.

Lane, 1983; Abhat, 1983; Garg et al., 1985; Buddhi, 1994; Hale et al., 1971; Sharma, 1999.

This would allow a designer to select the optimum operating temperature to obtain the maximum performance of a heat storage system. Sharma et al. (1999; 1998; 2002) have noticed that stearic acids melt over a wide range of temperature, have shown two melting points and have large variations in latent heat of fusion. But, they have thermally stable behavior after 1500 repeated melting / freezing cycles. The quality of stearic acid varies a lot in the commercial market due to their wide use in different products.

Therefore, no guarantee can be provided for their purity. This may be the reason that the latent heats of fusion of stearic acid generally decrease with the number of thermal cycles.

Salt Hydrates

Salt hydrates are the oldest and most studied heat storage

PCMs (Lane, 1983). They consist of a salt and water, which combine in a crystalline matrix when the material solidifies. They can be used alone or in eutectic mixtures (Abhat, 1983). Properties of some salt hydrates are given in Table 6. There are many different materials that have melting ranges of 15 to 117 °C (Lane, 1983). Salt hydrates are the most important group of PCMs, and have been extensively studied for their use in latent heat thermal energy storage systems. Three types of behavior of the melted salts can be identified: congruent, incongruent and semi- congruent melting. Congruent melting occurs when the anhydrous salt is completely soluble in its water of hydration at the melting temperature. Incongruent melting occurs when the salt is not entirely soluble in its water of hydration at the melting point. Semi-congruent melting occurs when the liquid and solid phases are in equilibrium during a phase transition.

Advantages. Low cost and easy availability of salt hydrates makes them attractive for heat storage applications (Lane, 1989). Two of the inexpensive and most available salt hydrates are $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ and $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ (Lane, 1983). Salt hydrates have a sharp melting point and high thermal conductivity when compared with other heat storage

PCMs. This can increase heat transfer in and out of the storage unit. They have a high heat of fusion, which decreases the needed size of the storage system. Salt hydrates also show a lower volume change than other PCMs. This makes it easy to design a container to accommodate volume change.

Disadvantages. Segregation is a formation of other hydrates or dehydrated salts that tend to settle out and reduce the active volume available for heat storage. Abhat (1983) reports a decrease in heat of fusion of over 73% in $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ after 1000 melt/ freeze cycles. This problem can be eliminated to a certain extent by using gelled or thickened mixtures (Lane, 1983), though this process negatively influences the heat storage characteristics of the mixture and the mixture still degrades with time (Abhat, 1983). Salt hydrates show super-cooling because they do not start to crystallize at the freezing point of other PCMs. This can be avoided using suitable nucleating materials to start crystal growth in the storage media. Lane (1983) offers a comprehensive listing of nucleating materials for most common salt hydrates. Abhat (1983) reports material degradation in $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ after only two cycles when the test sample was not hermetically sealed. Therefore, it is necessary to design containers to contain the material without letting water out. Another problem of salt hydrates is their tendency to cause corrosion in metal containers, which are commonly used in thermal storage systems (Abhat, 1983). Compatibility of a PCM and its container should always be checked before use.

Eutectics

A eutectic is a minimum melting composition of two or more components, each of which melts and freezes congruently, forming a mixture of the component crystals during crystallization (Lane, 1989). Eutectics nearly always melt and freeze without segregation because they freeze to an intimate mixture of crystals, leaving little opportunity for the components to separate. On melting, both components liquefy simultaneously, again with separation unlikely. A list of developed eutectics is given in Table 7.

Cross-linked Polyethylene

Cross-linked polyethylene is much like the polyethylene used in plastic bottles, except for the fact that it is lightly cross-linked to prevent it from turning into a liquid when it melts.

Like a liquid-solid PCM, it stores energy in the forming and breaking of its crystalline structure. Properties of two cross-linked polyethylenes are shown in Table 8. Cross-linked polyethylene is more stable than a liquid-solid PCM and can be used without encapsulation in another material.

Advantages. Although higher in cost than other PCMs, they do not need encapsulation. Therefore, low cost is attained for the entire heat storage system, and there are more feasibilities than with other PCMs. Cross-linked polyethylene is non-toxic and mostly chemically inert.

Disadvantages. The operating temperatures of 110 to 140 °C are too high for some applications such as space heating and water heating. To the author's knowledge, no company has commercially developed cross-linked polyethylene for heat storage applications at present.

Polyalcohols

Polyalcohols store energy in a structure change from a heterogeneous state at lower temperatures to a face-centered cubic form at higher temperatures (Wang et al, 2000). Poly-alcohols have many advantages over solid-liquid PCMs, such as small volume change, no leaking, and no degradation of the material (Wang et al, 2000). These advantages come with the disadvantages of low latent heat, high phase-change temperatures, and higher cost. Wang et al. (2000) reports a system of combining polyalcohols to adjust working temperatures. Some of his results are shown in Table 8 for Neopentyl Glycol (NPG)/Penaerythritol (PE) and Neopentyl Glycol (NPG)/Trihydroxy Methyl-Aminomethane (TAM) systems.

Commercial PCMs

Many companies (Climator, Cristopia, EPS Ltd., Mitsubishi Chemical Corporation, Rubitherm GmbH TEAP and Witco) are engaged in the development of PCMs for several applications. We tried to compile the commercially available PCMs for the temperature range 0 °C - 118 °C, and these are tabulated in Table 9

Latent Heat Storage Systems

The intermittent and dynamic nature of solar irradiance and the need to utilize solar energy systems in a continuous and static load make the use of storage systems essential in most of the potential uses of solar energy. The use of PCMs can be found in solar energy storage systems for water heating, green houses, space heating and cooling, cooking and waste heat recovery systems.

Solar Water Heater

Solar water heaters are getting popular (Buddhi et al., 1987; Tanishita, 1970) because they are relatively inexpensive and simple to fabricate and maintain. Prakesh et al. (1985) analyzed a built-in-storage type water heater containing a layer of PCM at the bottom (Fig. 2). During sunshine hours, the water gets heated, which in turn transfers heat to the PCM below it. The PCM melts and collects energy in the form of latent heat. During non-sunshine hours, the hot water is withdrawn and is substituted by cold water, which gains energy from the PCM. The energy is released by the PCM when changing its phase from liquid to solid. This type of system may not be effective due to the poor heat transfer between PCMs and water. Bansal and Buddhi (1992a) conducted an analytical study on cylindrical latent heat storage systems for domestic hot water (Fig. 3). During the charging mode of the PCM, the cylindrical capsule is in the closed loop with a solar water heater, and during the discharging mode, a liquid flowing through the storage unit extracts the energy. As a result, a theoretical model

for a cylindrical latent heat storage system was developed. The calculations for the interface-moving boundary and fluid temperature were made by using paraffin wax (p-116) and stearic acid as PCMs.

Tiwari et al. (1998) presented an analysis of PCM storage for a water heater by incorporating the effect of water flow through a parallel plate placed at the solid-liquid interface. In order to reduce the night heat losses from the exposed surface, a provision of covering the system by movable insulation was made. They concluded that the hot water (temperature $15\text{--}20\text{ }^{\circ}\text{C}$ $>$ ambient air temperature) can remain throughout the day and night, and the fluctuations in water temperature decrease with an increase in the melted region of the PCM water heater. Tayeb et al. (1993) developed a system for domestic hot water using $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ as a PCM and compared it with the simulation model that gives the optimum flow rate of the inlet water supply required to maintain the constant-temperature water at the outlet. Font et al. (1994) conducted a preliminary study for the design of a device for a domestic water heater using a solid-solid PCM. Numerical simulation has been made using a unidirectional model and verified with the experimental results. The concordance between both experimentally and simulation results shows that this model is available to study the heat transfer phenomenon in the PCM in order to optimize the design of the device.

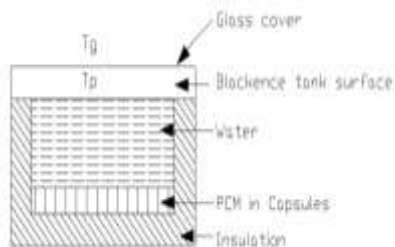


Figure 2 Built-in storage-type heater with PCM layer.

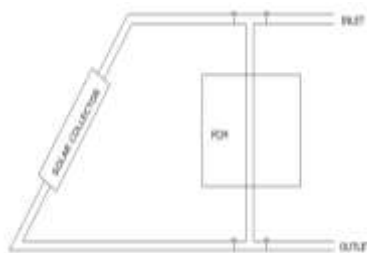


Figure 3 A domestic hot water system with separate latent heat storage unit.

Chauarsia (1986) and Gu et al. (2004) reported that paraffin wax could be used as a storage system for solar water heating. Baran and Sari (2003) reported the eutectic (melting point $52.3\text{ }^{\circ}\text{C}$, latent heat of fusion 182 kJ/kg) of palmitic acid (64.2 wt%) plus stearic acid (35.8 wt%) is suitable for domestic water heating applications. Bhargava (1983) utilized the PCM for a solar water heater and concluded that the efficiency of the system and the outlet water temperature during the evening hours increases with the increase in the thermal conductivity of the solid-liquid phases of the materials. Hasan et al. (1994) has investigated some fatty acids as PCMs for domestic water heating.

They recommended that myristic acid, palmitic acid and stearic acid, with melting temperature between $50\text{ }^{\circ}\text{C}$ - $70\text{ }^{\circ}\text{C}$ are the most promising PCMs for water heating. They concluded that a little reduction of the latent heat was found

after 450 heating cycles.

Kurklu et al. (2002) designed, developed and evaluated the thermal performance of a new type of water-PCM solar collector. The solar collector consisted of two adjoining sections, one filled with water and the other with a paraffin wax ($50\text{ }^{\circ}\text{C}$) as a PCM (Fig. 4). The results of the study indicated that the water temperature exceeded $55\text{ }^{\circ}\text{C}$ during a typical day of high solar irradiance and it was kept over $30\text{ }^{\circ}\text{C}$ for the whole night. This water-PCM solar collector has many advantages over the traditional solar hot water collectors in Turkey in terms of total system weight, cost and energy storage applications.

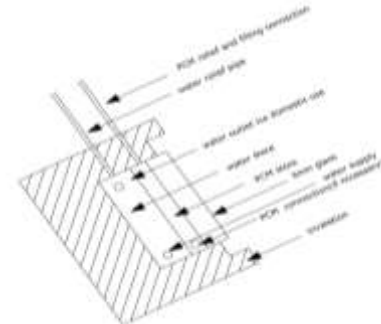


Figure 4 Water – PCM solar collector.

Recently, Canbazoglu et al. (2004) compared solar water heating systems with PCMs to conventional solar water heating systems. Fig. 5 shows a detailed cross-sectional view of a heat storage tank combined with a PCM. Polyethylene bottles were filled with a PCM and set into the tank as three rows. The total mass of PCM used in the heat storage tank was approximately 180 kg , using the density of the solid state of the PCM of 1666 kg/m^3 .

The bottles do not let the water flow in a horizontal direction due to their close location. Water flows through the vertical cavities between the bottles in the heat storage tank. The results indicate that the water temperature has a constant value of $46\text{ }^{\circ}\text{C}$ during the night until sunrise, as the hot water was not consumed. The difference between the temperatures at the midpoint of the heat storage tank and at the outlet of the collector of the heat storage tank with the PCM is greater, by an average value of approximately $6\text{ }^{\circ}\text{C}$, than that of the system without a PCM.

This temperature difference is considerable, exhibiting the high heat storage performance of the heat storage system with a PCM, during November. The storage time of hot water, the mass of hot water produced to use, and the total heat accumulated in the heat storage tank that contains some hydrated salts (used in the present study) are approximately 2.59–3.45 times greater than that of conventional solar energy systems with a heat storage tank that does not include a PCM. The thermal performances of hydrated salt-PCMs such as $\text{Na}_2\text{S}_2\text{O}_3 \cdot 5\text{H}_2\text{O}$, $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$, $\text{Na}_2\text{HPO}_4 \cdot 12\text{H}_2\text{O}$, $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ and $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ were examined theoretically. The hydrated salts with the highest solar thermal energy storage performance are $\text{Na}_2\text{HPO}_4 \cdot 12\text{H}_2\text{O}$ and $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$.

The additional cost for a PCM comes to around $\$0.5$ US per the unit volume of the heat storage tank in liters. However, the volume of a hot water tank required to store the same heat in energy storage systems including a PCM will be smaller than that of conventional solar energy storage systems. Therefore, it is obvious that the use of PCMs in the system may not cause an

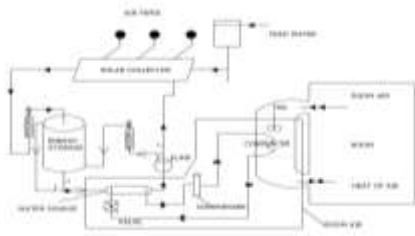


Figure 9 Solar-assisted heat pump system with latent heat storage tank.

When there is low or no solar radiation and the load is not zero during the night and on cloudy days, the cold water from the evaporator is sent to the tank instead of the collector. The cold water extracts heat from the PCM in the tank and it flows to the evaporator for use as a heat source. As a result, at night and cloudy times the stored energy in the tank is used as a heat source for the heat pump. The second mode occurs when solar irradiance is available for collection and the space-heating load is zero. In this mode, the hot water is circulated between the collectors and the tank only. He concluded that shorter and thinner pipes should be used for effective heating operations.

Normally, a solar air heater shows lower efficiency and inadequate storage capabilities. Fath et al. (1995) tried to increase the heat transfer rate and efficiency by replacing the conventional absorbers by a set of one-inch diameter tubes that act both as solar energy absorber and turbulence creator. The designed system is shown in Fig. 10. The tubes of the absorber of the collector were filled using thermal energy storage materials (sensible heat: sand and latent heat: paraffin wax; $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$). He concluded that using paraffin wax (melting point 50°C) as the latent heat storage material has the effect of damping out, flattening, and extending the effective period of high absorber and air outlet temperatures, and the effective heat rate. PCMs can maintain the absorbing temperature near the melting point, while the outlet air temperature was maintained almost constant for a long time, which can be useful in the utilization process. Based on a simple transient analysis, an explicit expression for the heater absorber and glass cover temperatures, effective gained heat, outlet air temperature, and the heater efficiency has been developed as a function of time. For the system with built-in PCM, the heat load could be provided for 24 hrs/day, at almost constant temperature. With paraffin wax, the outlet air temperature was maintained 5°C above the ambient temperature for about 16 h (almost 4 h after sunset). The daily average efficiency, with paraffin wax (melting point 50°C), is about 63.4% as compared to 59% with sand as the storage material and 38.7% for the conventional flat plate system. He recommended that $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ (melting point 32°C) should be used for lower ambient temperature and solar irradiance.

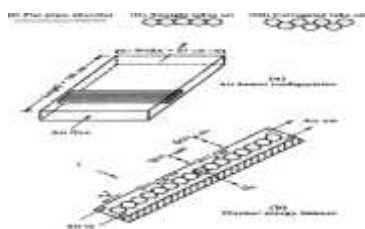


Figure 10 Solar air heater configuration with set of PCM tubes.

A number of researchers have proposed the inclusion of PCMs in walls, partitions, ceilings and floors to serve as temperature regulators. The PCMs have been used to replace masonry in a Trombe Wall. Experimental and theoretical tests have been conducted to investigate the reliability of PCMs as a Trombe Walls (Swet, 1980; Ghoneim et al., 1991). Bourdeau (1980) tested two passive storage collector walls using $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$. He concluded that an 8.1 cm PCM wall has slightly better thermal performance than a 40 cm-thick masonry wall. Askew (1978) used a collector panel made of a thin slab of paraffin wax and mounted behind the double-glazing of the building. Collier et al. (1979) showed that a macro-encapsulated PCM material cemented within masonry building blocks results in a significant increase in the system performance over an equivalent volume of concrete. Feldman (1970) studied the feasibility of construction of walls and partitions of cement blocks permeated with stearic acid as a PCM. They measured the storage capacity of these blocks and found it to be higher than cement blocks. Benard et al. (1985) experimentally tested paraffin Trombe Walls with double-glazing. The analysis of the results points out that a controlled air circulation would give good results.

Three thermal walls have also been examined using the same test-cell (Benard et al., 1982). This simulation was made with the help of two flat plate air-air heat exchangers totally covering the top and opposite inside walls of the cell.

The energy yield of the walls and the temperature variations of the inside room are compared for a 40 cm-thick concrete wall, an 8 cm-thick hard paraffin wall, and an 8-cm thick soft paraffin wall. Trombe Walls using paraffin are one-twelfth smaller than concrete walls and better suited to a retrofit. Strith et al. (2002) used Transparent Insulation Material (TIM) and translucent PCM in the wall for heating the air for the ventilation of the house. Paraffin wax (melting point $25\text{--}30^\circ\text{C}$, latent heat 150 kJ/kg) was used as a PCM, with 60 kg in a panel with the dimensions of $0.8 \times 1.8 \times 0.05\text{ m}$ for space heating. The efficiency of solar energy absorbed into the PCM and transferred to then ventilated air was 45% on average. Manz et al. (1997) also carry out the same study with another PCM ($\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$) as shown in Fig. 11. He proposed a numerical simulation, which fit well with experimental results. He reported that PCMs showed a positive effect and a higher utilization of solar gains can be expected. He also reported that the maximum time ratio parameter could be reached with a mean melting temperature of approximately 20 to 21°C when the building does not lose energy through the south facing TIM-PCM wall. He recommended further investigation in regard to the practical applications of the system in buildings, aspects of reliability, and durability. Arkar et al. (2002) also designed a solar-assisted ventilation system based on PCM storage. He recommended that paraffin-spherical encapsulations provide homogeneous porous effect in the ventilation duct, which can improve the thermal conductivity of paraffin. He reported that ambient air could be cooled for 3 to 4 K in a clear summer night.

Abhat (1981b) used a modular heat-pipe exchanger concept for use in a latent heat storage system for solar heating applications. The thermal analysis provides the influence of various geometric and thermal parameters on the storage charging time and temperature gradients for heat flow into two markedly different storage substances. Results indicate the capability of the heat exchanger concept to operate within small temperature swings ($>10\text{ K}$) for realistic heat input rates.

Comparisons between data and predictions of the test model showed adequate agreement. An active storage system for solar space heating and cooling (Fig.12) was developed (Maccracken, 1981). It consists of a close-spaced plastic tubing mat coiled into a spiral and inserted into a cylindrical tank containing PCM as a heat exchanger. The system contains salt hydrate as a PCM consisting of 98% sodium thiosulphate pentahydrate and two percent sodium sulfate for space heating applications and magnesium chloride hexahydrate for space cooling units. The plastic heat exchanger had the advantage of being low cost and being non-corrosive. 1.27 cm diameter plastic tubing with 2.5 cm spacing takes care of poor thermal conductivity of the PCM. The system was successfully tested for 1000 cycles without any degradation in the performance of the system.

A latent heat solar roof was tested in a Peruvian Village (altitude 3000m, latitude 13°S) to maintain near isothermal conditions in an experimental chicken brood (Benard et al., 1981). The brooder house was divided into two connecting parts, and a heated enclosure (Fig. 13). Two semi-circular tanks with their upper face closed with glass containing 42 kg of paraffin wax are located below an airtight glass roof. At night, thick polyurethane insulators were placed between the glass roof and paraffin tanks, which helps to regulate the temperature of the enclosure to stay between 22 °C and 30 °C. This temperature is suitable for breeding young chickens with the regularly renewed air.

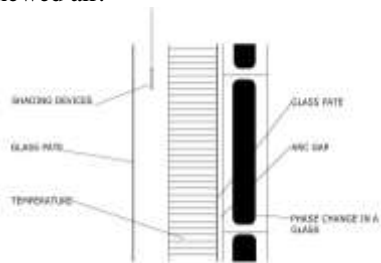


Figure 11 Prototype of TIM - PCM external wall system.

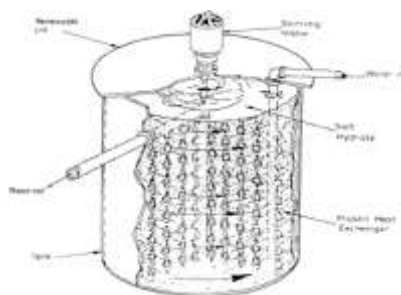


Figure 12 Calmac Corporation – PCM storage device.

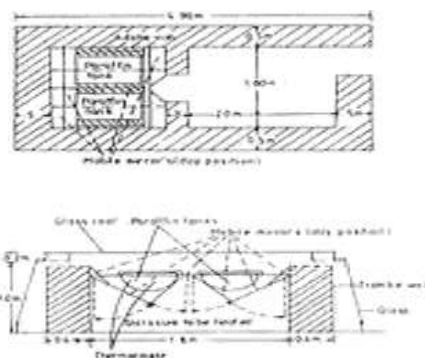


Figure 13 East west vertical cross section of a solar enclosure.

Various systems have been implemented, including an electrical floor heating system in Japan (Shumitomo Chemical, 2004). The most successful PCM thermal energy storage system is a large-scale heat storage system using spherical resin capsules (Mitsubishi Chemicals, 2004). PCM was also extensively used in building materials for passive utilization (Neeper, 2000; Feldman et al., 1995). Nevertheless, PCM takes a longer time to charge or discharge heat because of the thermal resistance of the solid phase on the inner wall. Therefore, direct heat exchange between the PCM and the medium can give higher heat transfer (Inaba et al., 1997b). A method in which micro-capsulated PCM is floated in a heating medium has been proposed (Shibutani, 2002). There are few examples of direct heat exchange with air as a heat transfer medium (Yamaha et al., 2001; Turpenny et al., 2000). A new type of heat storage system based on PCM granules consisting of porous media and paraffin wax has been proposed (Nagano et al., 2004a; Takeda et al., 2004). This system gives a simple mechanism for heat exchange and a high heat transfer coefficient. Numerical results show that the heat transfer coefficient and the proposed non-dimensional time can be used to estimate the amount of exchanged heat and the required time for phase change to be completed for different velocity and temperature conditions.

A theoretical model of a shell-and-tube PCM storage unit was reported Ismail et al. (1986). The numerical results show the effects of the Biot number, the relative diameters of the tubes, and the inlet fluid temperature on the thermal performance of the unit. Visser (1986) developed a component model for numerical description of two different short-term heat storage vessels.

In both vessels, the energy is stored as the latent heat of PCMs. The transient simulation program was used to determine the performance of the cylindrical energy storage tank, which can be used in solar assisted domestic heating by heat pump system. Yimmer and Adami (1989) suggested a numerical model for optimizing a basic one-dimensional, shell-and-tube type thermal energy storage system. Effects of the inner tube, outer shell radii and thermal conductivity of the PCM on the performance of the unit were discussed. A theoretical model to predict the transient behavior of a shell-and-tube latent heat storage unit was presented (Lacroix, 1993a). PCM was put in the shell and heat transfer fluid circulates inside the tubes. Effects of various thermal and geometric parameters on the heat transfer process and on the behavior of the system were confirmed.

Long-term performance of an air based solar heating system using a PCM was estimated (Sagara et al., 1994). Theoretical heat transfer models within PCM spherical capsules were studied. Effect on the overall coefficient of performance (COP) was studied with respect to the capacity of the PCM storage tank, melting temperature, collector area and air flow rate. They reported that the simple uniform temperature model is useful for long-term system simulations. Sari and Kaygusuz (2002) prepared a eutectic (lauric acid 75.5 wt% + stearic acid 24.5 wt%) with melting point at 37 °C and latent heat of 183 kJ/kg for passive solar space heating applications, such as building and greenhouse heating with respect to the climate conditions. Eutectic encapsulated in the annulus of two concentric pipes shows good heat transfer characteristics, and it has potential for heat storage in passive solar space heating systems.

A computer model was developed for space heating and cooling applications (Vakialtojjar et al., 2001). The effect of

PCM slab thickness and fluid passage gap on the storage performance was investigated. The author put the PCMs ($\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ and $\text{KF} \cdot 4\text{H}_2\text{O}$) in thin flat containers and air is passed through gaps between them. He concluded that the air velocity profile at the entrance does not affect the heat transfer characteristics and the outlet air temperature considerably. Using smaller air gaps and thinner PCM slabs can obtain better performance, however, this increases the number of PCM containers and the total volume of the storage system which will lead to higher-pressure drop across the storage system.

Several efforts have been made to develop PCM storage systems to utilize off peak electricity (Shitzer et al., 1983; Farid et al., 1990; Hatano et al., 1995; Lin et al., 2004). Using off peak electricity, PCM can melt to store electrical energy in the form of latent heat. Stored heat could utilize the peak period of electricity. Therefore, if latent heat storage systems are coupled with the active systems, it can help to reduce the peak load. Lin et al. (2004) analyzed the thermal performance of a room with an under-floor electric heating system with shape-stabilized PCM plates. This system can be used in various climates and will help to design such kinds of under-floor electric heating systems. Farid et al. (1990) used paraffin wax (55°C) encapsulated in a thin metal container to replace the ceramic bricks.

An electrical plate heater was fixed at the axis of each storage unit to provide low heat flux but sufficient to melt all the wax. During charging, PCM stores latent heat of melting, which is continuously discharged during the other periods. An electrical plate heater was fixed at the axis of each storage unit to provide low heat flux but sufficient to melt all the wax within 8 h. They concluded that latent heat storage systems could shift the peak-heating load. A floor heating system with $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ as a PCM was used for heating using off-peak electricity in Japan (Hatano et al., 1995).

Space Cooling

The most common storage media for space cooling are water, ice, and PCM, commonly known as eutectic salts. Ice has been used as a commercial PCM for years. Various technologies have been developed for ice storage. Some selected technologies for low temperature applications are: ice harvesting storage systems, external melt ice-on-coil storage systems, internal melt ice-on-coil storage systems and encapsulated ice. Normally, internal melt ice-on-coil systems and encapsulated ice systems use standard packaged chillers that have been configured to chill secondary coolants to ice-making temperatures. External melt systems may be installed with packaged chillers or with site assembled refrigeration plants. Ice harvesters use packaged or site assembled refrigeration systems (Dorgan, 1993).

PCMs have been used for various heat storage applications since the 1800s, but they have only recently been used as a storage media for space cooling. So far, most of the PCMs for cool storage are inorganic salt hydrates, organic paraffin waxes, and mixtures of these. A theoretical simulation of cool storage was reported (Solomar et al., 1989; BoHe et al., 2001). BoHe et al. investigated the potential for using cool storage systems using PCMs, and static and dynamic cool storage processes are discussed. They reported that the Rubitherm RT5 (melting point 7°C , latent heat of fusion 158.3 kJ/kg) appears to be an excellent candidate as a PCM for cool storage because of its economical cost, congruent melting, self-nucleation property, lack of super-cooling, and stability during a number of cooling

and heating cycles. They concluded that the volume contraction of the phase change process should not be neglected in a cooling storage system. If sufficient heat transfer area is available (e.g., floor or plant heat exchanger), the static storage system can be used. In the dynamic storage system, direct contact between the storage material and the heat transfer medium results in excellent heat transfer.

Identification of commercial PCMs for cool storage at $15\text{--}23^\circ\text{C}$ was carried out (Chemical Industry Report, 1988). Thermal characteristics of manganese (II) nitrate hexahydrate (melting point 25.8°C , latent heat of fusion 125.9 kJ/kg) as a PCM was examined for cooling applications (Nagano et al. 2003). They presented a general procedure for mixing and examination of PCMs for latent heat storage.

They reported that almost all chlorides were effective in modulating the melting point of $\text{Mn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$. $\text{MnCl}_2 \cdot 4\text{H}_2\text{O}$ was an effective additive with respect to modulation of melting point, reduction of super-cooling and quantity of the heat of fusion. The indoor air at temperature of 28°C in daytime and the outside cool air at night below 16°C can be utilized to melt and solidify this mixture.

Latent heat storage systems have been studied for air conditioning (Telkes, 1974; Gaorvon et al., 1977; Herrick, 1978). Inorganic hydrous salts have been used as storage material. Lane (1975) also suggested some PCMs for cooling and dehumidification. Farid et al. (1988) studied the feasibility of cool storage using dimethyl sulfoxide (melting point 16.5°C) as a PCM in a rectangular container. Based on the experimental results and the model predictions, dimethyl sulfoxide can be used as a PCM for cool storage. The results also show that, cooling extraction period depends on the amount of solidified PCM. The cool extraction period was completed when the outlet air temperature from the PCM section reached at 25°C . This temperature is considered the highest temperature at which the human may feel comfortable. An experimental and theoretical study was conducted for an encapsulated thermal storage tank (Saitoh and Hirose, 1986). They used $\text{Na}_2\text{HPO}_4 \cdot 12\text{H}_2\text{O}$ as PCM to fill cylindrical capsules with an inside diameter of 70.7 mm. They concluded that the main factors affecting the charging process were the capsule material, size, coolant flow rate and temperature. Kondepudi et al. (1988) also discussed the effect of Biot number, Stefan number, and Fourier number on the thermal performance of cold storage. Laybourn (1988) utilized a concept of thermal resistance, which embraced the convective resistance, wall resistance, and ice layer resistance to calculate the cold storage of the tank with rectangular capsules. Arnold (1990) analyzed the heat transfer during the freezing and melting process by performing a series of charging and discharging experiments. Chen et al. (1991a; 1991b; 1991c) developed a general lump model to predict the thermal performance of a cold storage system. The results showed that the lump model is a convenient and simple method to determine the thermal performance of a cold storage system. Ryu et al. (1991) used a rectangular storage tank with a copper tube container and conducted a series of experiments using both vertical and horizontal tank configurations to investigate heat transfer characteristics. Chen et al. (1991d) conducted a series of experiments to investigate the sub-cooling phenomenon and the freezing probability of water with and without nucleation agents inside a cylinder. They verified that the addition of nucleation agents is one of the approaches to improve the sub-cooling phenomenon effectively. Chen et al. (2000)

experimentally investigated the pressure drop of an encapsulated thermal storage tank during the charging process. The cylindrical capsules inside the thermal storage tank utilize water with nucleation agents added as PCM, and the coolant is the aqueous solution of ethylene glycol.

The results indicate that cool energy can be fully stored in the form of latent heat when the inlet coolant temperature is set below the temperature with 100% nucleation probability. They concluded that high cold storage could be obtained by using the lower inlet coolant temperature with high flow rate. The heat transfer coefficient increases as the coolant flow rate increases. The pressure drop flowing through tank is enlarged as the coolant flow rate increases during the charging process.

Greenhouse Heating

Solar agricultural greenhouses have been widely used in the past two decades in order to increase plant quality and productivity and to reduce consumption of fossil fuels for heating and cooling. The most effective greenhouses require control of temperature, humidity, solar irradiance and internal gas composition with rational consumption of energy (Boulard et al., 1990; Santamouris et al., 1994; Merritt et al., 1995; Marinkovi et al., 1998; Kurklu, 1998). Research work in this area, involving studies of new materials, heat storage and heat exchange devices resulted in some interesting demonstration units followed by rapid commercial applications. The most frequently used PCM for these purposes are $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$, $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$, PEG, and paraffins (Kurklu, 1998).

Kurklu (1998) has summarized work on greenhouses using PCM. $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ and $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ have been widely used because of low cost and high heat storage capacity with suitable melting point, but super-cooling and sensitivity towards moisture are serious disadvantages for long-term use. Nishina and Takakura (1984) used $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ with some additives to prevent phase separation and degradation for heating a greenhouse in Japan. Fig. 14 shows the general view of the experimental set-up. They concluded that 40 - 60% of the latent heat potential of the PCM was realized, which indicated that almost half of the PCM was not used efficiently during the energy exchange processes. Takakura et al. (1981) tested polyethylene glycol and $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ as PCMs in greenhouse

heating for 7.2 m² ground area. They compared conventional greenhouses with PCM storage type greenhouses. The efficiency of the greenhouse with PCM storage integrated with solar collector was 59% and able to maintain 8°C inside the greenhouse at night, when the outside temperature dropped to -6°C. A microcomputer control system has been developed in order to establish more accurate and more sophisticated control for solar greenhouse systems.

CNRE-France conducted a study for rose production in a 500 m² single glazed greenhouse by utilizing 13.5 tons of $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ (melting at 28°C) (Jaffrin and Cadier, 1982; 1987). Fig. 15 shows the arrangement of the PCM containers underground. The solar heat available inside the greenhouse was transferred and stored by recycling the air through an underground of flat heat exchangers filled with a PCM. The performance of the PCM greenhouse was compared with a traditional greenhouse of identical geometry having the same plantation. The PCM greenhouse achieved an 80% savings in propane gas as compared with the traditional greenhouse to maintain the same temperature. Latent heat storage materials

can also be stacked in racks placed in a greenhouse (Fig. 16), which will be directly heated by the solar radiation (Song, 1988). In this system, the hot air was circulated in the greenhouse through the storage to increase the rate of charging/discharging of PCM.

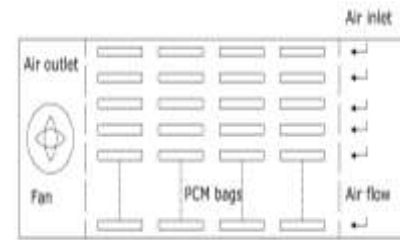


Figure 14 General view of phase change energy storage system.

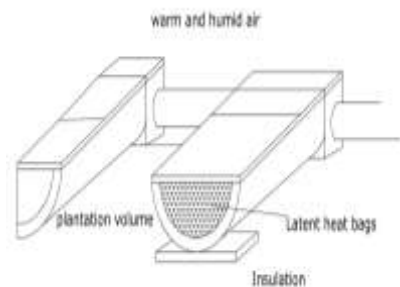


Figure 15 Underground tunnel: equipped with a PCM.

The stored heat was utilized during off sunshine hours to maintain the desired temperature of the greenhouse. $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ was used as PCM storage material in the greenhouse. Hung et al. (1975; 1983) had designed and constructed a latent heat storage system with two different stacking configurations and air baffling as an integrated part of the greenhouse solar system. Commercial cylindrical storage rods were used as the primary storage elements. The results showed that the designed latent storage systems demonstrated significantly higher compact storage capacity than the rock or water storage. It is revealed that the ring-baffled storage unit performed better than the cross-baffled storage unit.

Levav and Zamir (1987) tested $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ in greenhouses and reported that required air temperature in the greenhouse was achieved without any increase in the relative humidity. It was stressed that the most important drawback of the system was the high cost of the PCM. Furthermore, they indicated that the 24°C melting temperature of the PCM could be high for some crops. Kern et al. (1979) used $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ as a PCM in aerosol cans to investigate heat storage possibilities both inside and outside in a 36 m² ground area greenhouse covered with fiberglass. They reported that phase change storage system can provide a desirable alternative to rock storage. Paraffins have also been used for energy storage in greenhouses. A study performed by Bagetinelik et al. (1994) was the only work in the literature using paraffin (melting point 48–60 °C, latent heat of fusion 190 kJ/kg) for greenhouse heating.

Recently, Kfirli et al. (1996; 1997) used $\text{Na}_2\text{SO}_4 \cdot 10\text{H}_2\text{O}$ as a PCM in greenhouses. In their study, two types of a similar PCM, one with a melting range of 22–25°C and the other with one about 8°C, were employed, the former for the reduction of peak temperatures towards summer and the latter for frost prevention in greenhouses. Fig. 17 shows an experimental set-up of energy storage used in a greenhouse. They concluded that

solar collection efficiency with PCMs was 29% (at 22–25°C) and 30% (at 8°C) respectively. They suggested that PCMs could be used for both energy storage and humidity control in greenhouses. This helps manage energy effectively in greenhouses.

Enibe et al. (2002; 2003) designed, constructed and performed an evaluation of a natural circulation solar heating system using PCM energy storage. The system consists of a flat plate solar collector integrated with paraffin PCM for energy storage. The PCM is prepared in modules of thin rectangular blocks of PCM encapsulated by the rectangular walls of a box-like structure, which behaves like thin fins.

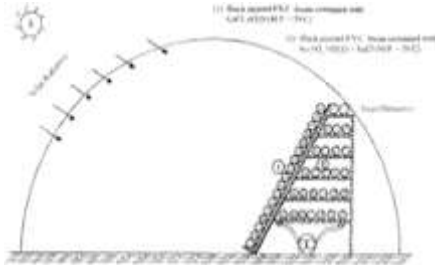


Figure 16 Greenhouse with PCM stacked in racks.

The encapsulating box is made of a material of good thermal conductivity, and divided into a number of compartments of identical dimensions. A number of such modules are equally spaced across the collector, as shown in Fig. 18 a & Fig. 18 b. The space between each module pair serves as an air heater, the heaters being connected to common air inlets and discharge header manifolds.

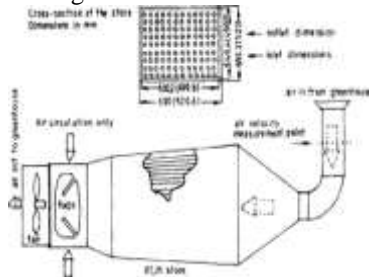


Figure 17 General view of the storage used for energy management in greenhouse.

By natural convection, ambient air enters the inlet header through control valve A, while heated air leaves the discharge header through valve B, flows into the hot air chamber, and is discharged to the environment through valve C. They concluded that the peak temperature rise of the heated air was about 15 K. The collective useful efficiency was about 50%. This system is suitable for use as a solar cabinet crop dryer for aromatic herbs, medicinal plants and other crops, which do not require direct exposure to sunlight.

Solar cooking

Solar cookers are used to cook rice, vegetables, meat, bake cakes, etc. The detailed design, testing, theory, and utility of box-type solar cookers are well developed (Telkes, 1959; Abhat 1981a; Mullick et al., 1987; Thulasi et al., 1994; Buddhi et al., 2000). The use of these solar cookers is limited because they do not have any storage, i.e., these cookers cannot be used on cloudy days or in the late evening. PCMs can be used for storing the solar heat in the form of latent heat in daytime; after that, stored heat can be used for evening / night cooking or on cloudy days (Domanski et al., 1995; Buddhi and Sahoo, 1997; Sharma et al., 2000; Buddhi and Sharma, 2003). A box-type solar cooker with PCM was designed and fabricated for the composite climatic conditions of India (Buddhi and Sahoo,

1997). Commercial-grade stearic acid (melting point 55 °C, latent heat of fusion 161 kJ/kg) was used as a PCM.

Fig. 19 shows the sketch of a box-type solar cooker for one vessel using a PCM to store the solar energy. In the center of the absorbing plate 'A,' a cylindrical container of 0.165 m diameter and 0.02 m in depth was welded (shown in Fig. 18 by 'C'), and the cooking pot is to be kept tightly in it.

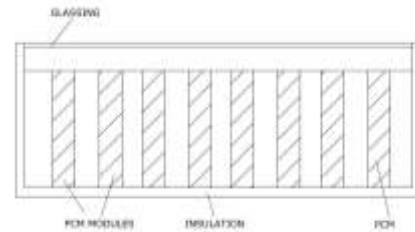


Figure 18a Cross-section view of collector assembly with PCM.

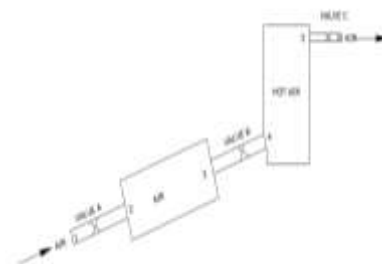


Figure 18b Schematic diagram of natural circulation air heater with PCM.

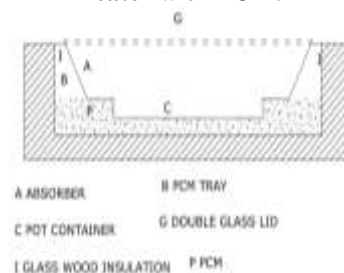


Figure 19 Schematic diagram of the box of a solar cooker with PCM storage.

This container will provide a heat transfer from the absorbing plate and PCM. Moreover, aluminum fins were also provided at the inner side of the tray and cylindrical container. The outer tray 'B' is also made from the same aluminum sheet. The distance between tray 'A' and tray 'B' was kept at 0.025 m on the bottom side. Tray 'B' was filled with 3.5 kg of commercial grade stearic acid (PCM) and it was made sure that the PCM was in good contact with the bottom side of tray 'A.' The space between tray 'B' and the casing was filled with glass wool to provide thermal insulation to the bottom and sides of the solar cooker. A flat glass mirror was fixed in an aluminum cover to serve as a booster and as a cover for the glass lid when the cooker is not exposed to solar radiation. The aluminum tray 'A,' cooking pot and its cover were painted with a dull black paint on the outside. The experimental results demonstrate the feasibility of using a PCM as the storage medium in solar cookers, i.e., it is possible to cook the food even in the evening with a solar cooker having latent heat storage. It also provides a nearly constant plate temperature in the late evening.

Domanski et al. (1995) investigated the possibility of cooking during non-sunshine hours using PCM. They designed

the storage-cooking vessel for non-sunshine hours (Fig. 20). For this purpose, two concentric cylindrical vessels (0.0015 m thick), made from aluminum, are connected together at their tops using four screws to form a double-wall vessel with a gap between the outer and inner walls. The outer and inner vessel have a diameter of 0.18 m and 0.14 m. The annular gap between the outer and inner vessels is 0.02 m. This gap is covered with a removable aluminum cover into which three circular holes were drilled to allow inserting of thermocouples and permit direct visualization during filling or removing of the PCMs. A circular aluminum cover is used as the lid for the inner vessel. The gap between the outer and inner vessels was filled with 1.1 kg of stearic acid (69 °C), or 2.0 kg of magnesium nitrate hexahydrate (89 °C), which leaves sufficient space for expansion of the PCMs on melting. Cooker performance was evaluated in terms of charging and discharging times of the PCMs under different conditions. They reported that performance depends on the solar irradiance, mass of the cooking medium, and the thermo physical properties of the PCM. The overall efficiency of the cooker during discharging was found to be 3-4 times greater than that for steam and heat-pipe solar cookers, which can be used for indoor cooking. In such a type of design, the rate of heat transfer from the PCM to the cooking pot is slow, and more time is required for cooking the evening meal.

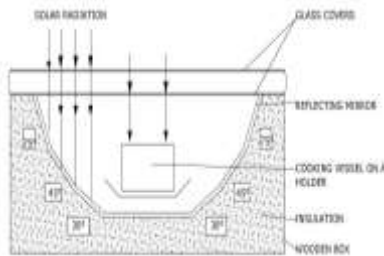


Figure 20 Solar cooker with PCM cooking container.

Sharma et al. (2000) designed and developed a cylindrical PCM storage unit for a box-type solar cooker to cook the food in the late evening. Because this unit surrounds the cooking vessel, the rate of heat transfer between the PCM and the food is higher, and cooking can be faster. For this purpose, a PCM container to hold the cooking vessel was designed and fabricated as shown in Fig. 21. It has two hollow concentric aluminum cylinders of diameters 18 cm and 25 cm, and is 8 cm deep with a 2 mm thickness. The space between the cylinders was filled with acetamide (melting point 82 °C, latent heat of fusion 263 kJ/kg) as a PCM. The dimensions of the vessel used for cooking were 17.5 cm and 10 cm in diameter and height, respectively, and it can be inserted inside the PCM container for cooking purposes. To enhance the rate of heat transfer between the PCM and the inner wall of the PCM container, eight fins (1x3 cm) were welded at the inner wall of the PCM container. They reported that by using 2.0 kg of acetamide as a latent heat storage material, the second batch of food could be cooked if it is loaded before 3:30 P.M. during the winter season.

They recommended that the melting temperature of a PCM should be between 105 and 110 °C for evening cooking. Therefore, there was a need to identify a storage material with appropriate melting point and quantity, which can cook the food in the late evening. To store a larger quantity of heat in a PCM, more input solar radiation would be required. Hence, Buddhi and Sharma (2003) used a latent heat storage unit for a box type solar cooker with three reflectors. They used acetanilide (melting point 118 °C, latent heat of fusion 222 kJ/kg) as a

PCM for night cooking. To conduct the cooking experiments with the PCM storage unit, a double glazed (glass covers) box-type solar cooker having a 50 cm×50 cm aperture area and being 19 cm deep was used.

In this solar cooker, three reflectors were provided, i.e., the middle reflector was mounted with a hinge and had rotation only about the horizontal axis. The other two reflectors were fixed by a ball and socket mechanism in the left and right sides of the reflector.

This pair of reflectors has three degrees of freedom, i.e., they can have movement about the horizontal axis, and vertical axis and can rotate about both the axes. By these mechanisms, efforts were made to keep the reflected solar irradiance on the absorber surface to enhance the incident solar radiation on the glass cover during the course of the sun exposure experiments.

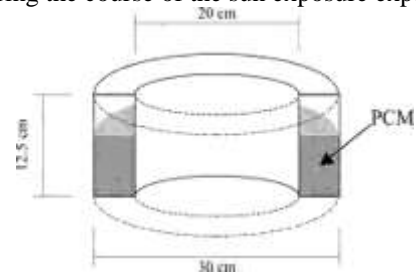


Figure 21 A schematic diagram of the latent heat storage unit.

Following Sharma et al. (2000), a cooking vessel with latent heat storage was designed and fabricated to cook the food in night. The unit has two hollow concentric aluminum cylinders of diameter 20 and 30 cm, and is 12.5 cm deep and 2 mm thick. The space between the cylinders was filled with 4.0 kg of PCM to conduct the cooking experiments with all three reflectors.

The dimensions of the vessel used for cooking were 19 and 15 cm in diameter and height, respectively, and it can be inserted inside the PCM storage unit for cooking purposes.

To enhance the rate of heat transfer between the PCM and the inner wall of the PCM container, eight fins (1 cm× 3 cm) were welded at the inner wall of the PCM container. From the experimental results, one can conclude that the cooking experiments were successfully conducted for the evening time, cooking up to 8 P.M. with 4.0 kg of PCM during winter season in India.

Sharma et al. (2004) developed a solar cooker based on Evacuated Tube Solar Collector (ETSC) with PCM storage, as shown in Fig. 22. It consists of an ETSC, a closed loop pumping line-containing water as Heat Transfer Fluid (HTF), a PCM storage unit, cooking unit, pump, relief valve, flow meter, and a stainless steel tubing heat exchanger.

The PCM storage unit has two hollow concentric aluminum cylinders, and its inner and outer diameters are 304 mm and 441 mm, respectively, and is 420 mm deep and 9 mm thick (Fig. 23). The space between the cylinders was filled with 45 kg erythritol (melting point 118 °C, latent heat of fusion 339.8 kJ/kg) used as the PCM.

A pump circulates the heated water (HTF) from the ETSC through the insulated pipes to the PCM storage unit by using a stainless steel tubing heat exchanger that wraps around the cooking unit by closed loop.

During sunshine hours, heated water transfers its heat to the PCM and is stored in the form of latent heat through a stainless steel tubing heat exchanger.

This stored heat is utilized to cook the food in the evening time or when sun intensity is not sufficient to cook the food.

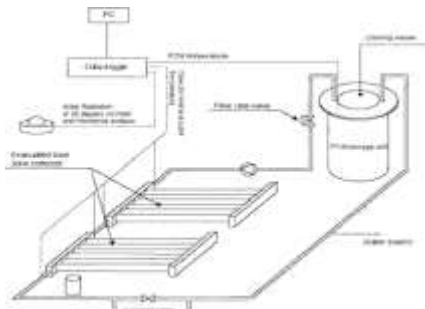


Figure 22 Outline of the prototype solar cooker based on evacuated tube solar collector with PCM storage unit.

They concluded that two cooking times (noon and evening) were in a day. Noon cooking did not affect the cooking in evening, and evening cooking using PCM storage was found to be faster than noon cooking. Experiments and analysis indicated that the prototype solar cooker yielded satisfactory performance in spite of low heat transfer; the modified design of heat exchanger in the thermal storage unit will enhance the rate of heat transfer in the present set-up. Ramadan et al. (1987) designed a simple flat-plate solar cooker with focusing plane mirrors using energy storage materials. In his design, a jacket of sand (1/2 cm thick) around the cooking pot has improved the cooker performance tremendously. They concluded that six hours per day of cooking time have been recorded. Approximately three hours per day of indoor cooking has been achieved. Overall energy conversion efficiency up to 28.4% has been obtained.

The possibility of using a PCM as a storage medium to obtain longer cooking periods was studied. A thin layer of the salt hydrate $\text{Ba}(\text{OH})_2 \cdot 8\text{H}_2\text{O}$ as a jacket around the cooking pot was suggested. Bushnell (1988) presented a prototype for solar ovens, which employ pentacrythritol as a solid-solid PCM. He described the performance from efficiency measurements and determination of figure of merit.

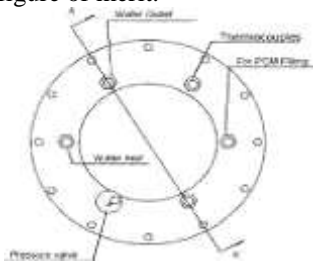


Figure 23a Verticalview of the PCM storage unit.



Figure 23b Verticalview of the PCM storage unit.

Waste Heat Recovery Systems

Air conditioning system eject (sensible and latent) heat, in which sensible heat accounts for about 15–20% of the total exhausting heat (Zhang, 1999). The exhausting temperature of the compressor is relatively high ($<65^\circ\text{C}$) when using Freon as refrigerant.

Therefore, it can be recovered using an accumulator and gets heat of higher temperature. Gu et al. (2004) developed a heat recovery system using PCM to recover the rejected heat of

air conditioning systems and produce low temperature hot water for washing and bathing. They concluded that the heat recovery system decreases not only the consumption of primary energy for heating domestic hot water but also the calefaction to the surroundings due to the rejection of heat from air conditioning systems.

It was observed that the efficiency ratio of the system is improved effectively when all the rejected (sensible and latent) heat from air conditioning systems is recovered. The technical grade paraffin wax and the mixtures with liquid paraffin and lauric acid qualify as PCM for heat recovery of air conditioning systems.

An effective utilization of urban waste heat from co-generation systems is typically available at temperatures of $60\text{--}100^\circ\text{C}$. Ona et al. (2001) have investigated erythritol (melting point 118°C ; latent heat of fusion 339.8 kJ/kg) that can be used for relatively high temperature industrial waste heat processes. Several studies have been done on stearic acid (Buddhi and Sharma, 1999; Sari and Kaygusuz, 2001). This material has a melting point between $60\text{--}70^\circ\text{C}$ and is expensive. It has only been found to be of limited use in waste heat systems.

Nagano et al. (2004b) proposed a mixture of $\text{Mg}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ as a base material with $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ as an additive to modulate the melting point. They reported that the addition of 5–10 wt% of $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ can set the $\text{Mg}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (melting point 80°C , latent heat of fusion 150 kJ/kg). Increasing the mix ratio had little effect on heat of fusion, but allowed the melting point to be reduced to about 60°C . No degradation in the melting point and latent heat of fusion were observed after 1000 accelerated thermal cycles.

Yagi et al (1995) conducted a fundamental study on heat transfer for developing a heat storage process by latent heat for recovering high temperature waste heat over 500 K . Heat transfer experiments were attempted for a single encapsulated phase change material and for a packed bed.

The metal PCMs were found to be excellent for heat storage because of uniform temperature in the capsule. Simulation results show that the concurrent flow for heat storage and release showed better results for effective use of storage heat than counter-current flow.

Buddhi (1997) designed and fabricated a shell and tube type heat exchanger for low temperature waste heat recovery using PCM (Fig. 24). Stearic acid (59°C , 198 kJ/kg) was used as a PCM for this study. To enhance the effective thermal conductivity of the system, the radial distance between the tubes was kept at 3 to 4 cm.

The shell was filled with 50 kg commercial grade stearic acid. Hot and cold water was used as a Heat Transfer Fluid (HTF) for charging / discharging of the PCM. Ambient temperature, flow rate and PCM temperatures were measured simultaneously at an interval of 15 minutes.

He concluded that the experimental results show the feasibility of using PCM as storage media in heat recovery systems. Due to poor thermal conductivity of the PCM the overall heat transfer coefficient is quite low and fins should be provided to increase the effectiveness of the heat exchanger. Distance between tubes, fins, and mass flow rates should be selected care- fully in order to optimize the performance of the heat exchanger. Paraffin wax (54°C , 184 kJ/kg) was also used in a shell and tube type heat exchanger for waste heat recovery (Buddhi, 2003). Fins were also used for effective heat transfer.

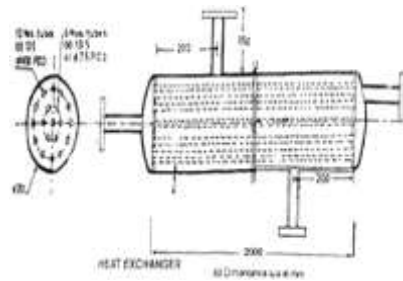


Figure 24 Shell and tube type heat exchanger with latent heat storage material.

Heat Transfer Enhancement

In a latent heat storage system, the solid-liquid interface moves away from the heat transfer surface during phase change. During this process, the surface heat flux decreases due to the increasing thermal resistance of the growing layer thickness of the molten / solidified medium. In the case of solidification, conduction is the only transport mechanism, and in most cases, it is very poor. In the case of melting, natural convection can occur in the molten layer and this generally increases the heat transfer rate compared to the solidification process (if the layer is thick enough to allow natural convection to occur). However, the generally low heat transfer rate can be increased considerably by using a suitable heat transfer enhancement technique. There are several methods to enhance the heat transfer in latent heat storage system. The use of finned tubes with different configurations has been proposed by various researchers as an efficient means to improve the charge/discharge capacity of a latent heat storage system (Sparrow et al., 1981; Eftekhari et al., 1984; Kamimoto et al., 1986b; Padmanabhan and Murty, 1986; Morcos, 1990; Choi and Kim, 1992; Hoogendoorn and Bart, 1992; Lacroix, 1993b; Khan et al., 1994; Tong et al., 1996; Velraj et al., 1997; Costa et al., 1998; Bauer and Wirtz, 2000). Other heat transfer enhancement techniques are having the PCM inserted in a metal matrix (Stovall et al., 1988; Hafner and Schwarzaer, 1999), using PCM dispersed with high conducting particles (Siegel, 1977), micro encapsulation of PCM (Mulligan et al., 1996; Bedecarrats et al., 1996), embedded graphite matrix (Mehling et al., 1999; Py et al., 2001), carbon fiber brushes with a high thermal conductivity (190 W/mK) (Fukai et al., 2002), exfoliated graphite (EG) for improving the thermal conductivity of the form-stable P/HDPE composite PCMs (Sari et al., 2004), copper plates inserted in spherical capsules for n-octadecane PCM (Koizumi, 2004), using metal screens/spheres placed inside the PCM (Etouney et al., 2004).

Erik and Dudukovic (1996) presented a novel energy storage system consisting of n-octadecane retained by capillary forces in a porous silica support. This configuration eliminates the expensive heat exchange surface, provides higher energy density, and gives higher rates of energy storage and release. Leoni and Amon (1997) employed aluminum foam to enhance the heat transfer process in latent heat storage system.

Encapsulation of PCMs

Encapsulation has two containment methods, macro and micro encapsulation. Macro- encapsulation comprises the inclusion of PCM in some form of package such as tubes, pouches, spheres, panels or other receptacles. These containers can serve directly as heat exchangers or they can be incorporated in building products. Previous experiments with macroencapsulation failed due to the poor heat transfer rate. The PCM freezes on the heat exchanger surface resulting in a poor

heat transfer rate due to the low thermal conductivity of PCMs. Many attempts have been made to overcome these difficulties. A new technique "microencapsulation" of PCMs was studied in the late 1970s after PCMs had long been employed as the thermal storage and control materials (Colvin, 1999). Microencapsulation is the packaging of micronized materials (both liquids and solids) in the form of capsules, which range in size from less than 1 mm to more than 300 mm. The wall material of the capsule can be formulated by using a wide variety of materials including natural and synthetic polymers. There are many advantages of microencapsulated PCMs, such as increasing heat transfer area, reducing PCM reactivity towards the outside environment and controlling the changes in the storage material volume as phase change occurs.

Macroencapsulation of $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ in plastic and metal containers appears promising for heating systems using air as the heat transfer medium (Lane, 1980). After considering a number of heating and cooling schemes employing phase change heat storage, a forced hot air, central storage design using $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ encapsulated in plastic pipes was adapted. Microencapsulation also allows the PCM to be incorporated simply and economically into conventional construction materials (Fraunhofer ISE, 2002). Plastic or metallic encapsulation of the PCM is expensive but safe, as the PCM is not in contact with the concrete. Microencapsulation by impregnating the PCM in the concrete is very effective, but it may affect the mechanical strength of the concrete. Polymerization of PCMs has been also studied for other applications, like insulation materials for use in clothing or bedding articles (Salzer, 1999). Inaba et al. (1997a) and Lee et al. (1998) proposed shape stabilized paraffin (74% paraffin and 26% HDPE) integrated with the building materials without encapsulation. Structural stability is achieved using HDPE, which retains the paraffin when in liquid phase.

Experiments and simulations have been conducted to evaluate the characteristics and performance of encapsulated paraffin in crosslink agents in terms of encapsulation ratio and energy storage capacity (Hawladar et al., 2002). It was found that a higher coating to paraffin ratio led to a higher paraffin encapsulation ratio and then lower product hydrophilicity. Thermal cyclic tests showed that the encapsulated paraffin kept its geometrical profile and energy storage capacity even after 1000 cycles of operation.

A new material for low temperature storage was developed (Royon et al., 1997). They contained the water as a PCM within a three dimensional network of polyacrylamide during the polymerization process. The final material remains well shaped, requiring no support or even coating, so it can be used directly. Recently a compound PCM, which consists of paraffin (75%) as a dispersed PCM and a HDPE (25%) as a supporting material was developed (Hong et al., 2000). The developed PCM (melting point 57 °C, latent heat of fusion 157 kJ/kg) is suitable for application in direct contact heat exchangers. PCM microencapsulation has been developed by many companies (Jahns, 1999). Microencapsulated PCMs can be included within textile fibers; composites and clothing to provide greatly enhanced thermal protection in both hot and cold environments (Colvin et al., 1998).

The potential use of microencapsulated PCMs in various thermal control applications is limited because of the cost. However, thermal control for space applications is more

important than the cost; researchers believe that the development of such PCMs could be a milestone for space technology (Mulligan et al., 1996).

New PCM Innovations

Revankar (2001) presented a new testing method for satellite power using latent heat storage. PCM becomes liquid under high temperature, which then freezes during hours of cold darkness and releases its latent heat. The released heat can be used to generate electricity by driving thermoelectric units. John et al. (2000) designed a novel ventilation nighttime cooling system (a novel combination of PCM and heat pipes) as an alternative to air conditioning. The system offers substantial benefits in terms of reducing or eliminating the need for air conditioning.

Cabeza et al. (2002) reported that the PCM can be used for transporting temperature-sensitive medications and food because of the PCM's capability to store heat and cold in a range of several degrees. Several companies are engaged in the research of temperature sensitive transporting PCMs for various applications [237 - 241].

Vasiliev et al. (2000) developed the latent heat storage module for motor vehicles so the heat is stored when the engine is stopped, and can be used to preheat the engine on a new start. It is possible to reach an optimized working temperature within the engine in a much shorter time using heat storage than without heat storage. Pal and Joshi (1996; 1997) recommended the PCM to restrict the maximum temperature of electronic components. Tan et al. (2004) conducted an experimental study on the cooling of mobile electronic devices, such as personal digital assistants (PDAs) and wearable computers, using a heat storage unit (HSU) filled with the phase change material (PCM) of n-eicosane inside the device. The high latent heat of n-eicosane in the HSU absorbs the heat dissipation from the chips and can maintain the chip temperature below the allowable service temperature of 50 °C for 2 h of transient operations of the PDA.

Ulfvengren (2004) from Climator has developed a cooling vest for athletes for reducing body temperature. PCMs have also been proposed for cooling a newborn baby (Olsson, 2004). Phase change technologies can also be used for cryosurgery, which is a technique for destroying the unwanted cells by freezing and thawing (Alexiades and Solomon, 1992). Koschenz et al. (2004) developed a thermally activated ceiling panel for incorporation in lightweight and retrofitted buildings. It was demonstrated, by means of simulation calculations and laboratory tests, that a 5 cm layer of microencapsulated PCM (25% by weight) and gypsum surface will maintain a comfortable room temperature in standard office buildings. Paraffins, namely, Hexadecane was tried as a PCM in this prototype set-up. Naim et al. (2002) constructed a novel continuous single-stage solar still with PCM. They reported that the productivity of a solar still can be greatly enhanced by the use of a PCM integrated to the still.

Huang et al. (2004) used PCMs for thermal regulation of building-integrated photo-voltaics. Depending on ambient conditions, a PV/PCM system may enable the PV to operate near its characterizing temperature (25 °C). They developed PV/PCM simulation model and validated it with experimental results. The improvement in the thermal performance achieved by using metal fins in the PCM container is significant. The fins enable a more uniform temperature distribution within the PV/PCM system to be maintained. An extensive experimental test has been undertaken on the thermal behaviour of a phase

change material, when used to moderate the temperature rise of PV in a PV/PCM system (Huang et al., 2000; 2001; 2002; Tavaranan et al., 2002). Use of PCM with photovoltaic (PV) panels and thermoelectric modules (TEMs) in the design of a portable vaccine refrigerator for remote villages with no grid electricity was proposed by Tavaranan et al. (2002). TEMs, which transfer heat from electrical energy via the Peltier effect, represent good alternatives for environmentally friendly cooling applications, especially for relatively low cooling loads and when size is a key factor. Thermoelectric refrigeration systems employing latent heat storage have been investigated experimentally by Omer et al. (2001). Trelles and Duffy (2003) proposed a numerical simulation of a porous latent heat thermal energy storage device for thermoelectric cooling under different porosities of the aluminum matrix. They used a porous aluminum matrix as a way of improving the performance of the system, enhancing heat conduction without reducing significantly the stored energy.

Weinlader et al. (2004) used PCM in double-glazing façade panel for day lighting and room heating. A facade panel with PCM shows about 30% less heat losses in south-oriented facades. Solar heat gains are also reduced by about 50%. Facade panels with PCM improve thermal comfort considerably in winter, especially during evenings. In summer, such systems show low heat gains, which reduces peak cooling loads during the day. Additional heat gains in the evening can be drawn off by nighttime ventilation. If a PCM with a low melting temperature of up to 30 °C is used, thermal comfort in summer will also improve during the day, compared to double glazing without or with inner sun protection. A homogeneous appearance of the PCM-systems is achievable by use of concealment, like a screen print glazing.

Ying et al. (2004) developed the test standards for PCM fabrics. Three indices have been proposed to characterize the thermal functional performance of PCM fabrics. The index of thermal regulating capability can describe the thermal regulating performance of PCM fabrics, and is strongly dependent on amount of PCM. Khateeb et al. (2004) designed a lithium-ion battery employing a novel phase change material (PCM) for thermal management systems in an electric scooter. Developed Li-ion battery was suggested in order to replace the existing lead-acid battery in the electric scooter without introducing any mechanical changes in the battery compartment.

Concluding Remarks

From the various issues discussed above it may be summed up that,

- Adoption of PCM in the Latent Heat Energy Storage systems give more energy in less space.
- PCMs gives more comfort for space heating and space cooling applications.

Some of the key issues and future directions put forth here are the views of the authors based on the knowledge acquired and experience gained from the review of the literatures presented here. However, the perspectives and directions in the near future will depend on the needs of the society and the developments in related areas.

Acknowledgement

The authors are thankful to the knowledge society and well wishers. Further, it is with unbounded gratitude and heartfelt happiness that we wish to bestow thanks on each and everyone for their remarkable encouragement, support and assistance rendered to prepare this review article.

References

1. Abhat, A. (1981a). Short term thermal energy storage. *Energy and Buildings* 3(1): 49–76.
2. Abhat, A. (1981b). Development of a modular heat exchanger with integrated latent heat storage. Report No. BMFT FBT 81–050. Germany Ministry of Science and Technology, Bonn Germany.
3. Abhat, A. (1983). Low temperature latent heat thermal energy storage: heat storage materials. *Solar Energy* 30 (4): 313–331.
4. Aboul-Enein, S., Olofa, S.A. (1991). Thermophysical properties of heat-of-fusion storage materials for cooling applications. *Renewable Energy* 1(5 - 6): 791–797.
5. Alexiades, V., Solomon, A.D. (1992). *Mathematical Modeling of Melting and Freezing Process*. Washington, DC Hemisphere Publishing Corporation.
6. Arkar, C., Medved, S. (2002). Enhanced solar assisted building ventilation system using sphere encapsulated PCM thermal heat storage. IEA ECES IA Annex 17. *Advanced Thermal Energy Storage Techniques – Feasibility Studies and Demonstration Projects 2nd Workshop*. Ljubljana, Slovenia (<http://www.fskab.com/Annex17>).
7. Arnold, D. (1990). Dynamic simulation of encapsulated ice stores-part I: the model. *ASHRAE Trans* 97(2): 1170–1178.
8. Askew, G.L. (1978). Solar heating utilization a paraffins phase change material. *Proceedings of the 2nd National Passive Solar Conference*. Philadelphia, PA. March 16–18.
9. Babich, M.W., Hwang, S.W., Mounts, R.D. (1992). The search for novel energy storage materials using differential scanning calorimetry. *Thermochemica Acta* 210: 83–88.
10. Bagetinelik, A., Demirel, Y., Paksoy, H.O., Oztifirk, H.H. (1994). Greenhouse heating with solar energy stored by phase change material. *15th National Agricultural Mechanisation Congress*. Antalya, Turkey: 698–705.
11. Banaszek, J., Domanaski, R., Rebow, M., El-Sagier, F. (1999). Experimental study of solid - liquid phase change in a spiral thermal energy storage unit. *Applied Thermal Engineering* 19: 1253–1277.
12. Bansal, N.K., Buddhi, D. (1992a). An analytical study of a latent heat storage system in a cylinder. *Energy Conversion and Management* 33 (4): 235–242.
13. Bansal, N.K., Buddhi, D. (1992b). Performance equations of a collector cum storage system using phase change materials. *Solar Energy* 48(3): 185–194.
14. Baran, G., Sari, A. (2003). Phase change and heat transfer characteristics of a eutectic mixture of palmitic and stearic acids as PCM in a latent heat storage system. *Energy Conversion and Management* 44: 3227–3246.
15. Bathelt, A.G., Viskanta, R. (1980). Heat transfer at the solid-liquid interface during melting from a horizontal cylinder. *International Journal of Heat and Mass Transfer* 23(11): 1493–1503.
16. Bauer, C., Wirtz, R. (2000). Thermal characteristics of a compact, passive thermal energy storage device. In: *Proceedings of the ASME IMECE*, Orlando, USA.
17. Bedecarrats, J.P., Strub, F.P., Falcon, B., Dumas, J.P. (1996). Phase-change thermal energy storage using spherical capsules: performance of a test plant. *Int J Refrig* 19(3): 187–196.
18. Bellecci, C., Conti, M. (1993). Phase change thermal storage: transient behaviour analysis of a solar receiver/storage using the enthalpy method. *International Journal of Heat and Mass Transfer* 36:2157–2163.
19. Benard, C., Body, Y., Gobin, D., Guerrier, B. (1982). Use of a variable parameter test-cell for the study of latent-heat solar walls. *Solar Energy* 29(2): 101–109.
20. Benard, C., Body, Y., Zanolli, A. (1985). Experimental comparison of latent and sensible heat thermal walls. *Solar Energy* 34(6): 475–487.
21. Benard, C., Gobin, D., Gutierrez, M. (1981). Experimental results of a latent heat solar roof used for Bhargava, A.K. (1983). Solar water heater based on phase changing material. *Applied Energy* 14(3):197–209.
22. Boulard, T., Razafinjohany, E., Baille, A., Jaffrin, A., Fabre, B. (1990). Performance of a green- house heating system with a phase change material. *Agricultural and Forest Meteorology* 52 (3–4):303–318.
23. Bourdeau, L.E. (1980). Study of two passive solar systems containing phase change material for thermal storage. *Proceedings of the 5th National Passive Solar Conference*. Amherst, MA. October 19–26.
24. Buddhi, D. (1997). Thermal performance of a shell and tube pcm storage heat exchanger for industrial waste heat recovery. *Proc ISES Solar World Congress*. Taejon, Korea. August 24–29.
25. Buddhi, D. (2003). Experimental thermal performance evaluation of a heat exchanger having PCM for storage of waste heat. IEA ECESIA Annex 17. *Advanced Thermal Energy Storage Through Phase Change Materials And Chemical Reactions – Feasibility Studies And Demonstration Projects 4th Workshop*. Indore, India (<http://www.fskab.com/Annex17>).
26. Buddhi, D., Sahoo, L.K. (1997). Solar cooker with latent heat storage: design and experimental test- ing. *Energy Conversion and Management* 38 (5): 493–498.
27. Buddhi, D., Sawhney, R.L. (1994). Proceeding of thermal energy storage and energy conversion.
28. School of energy and environmental studies. Devi Ahilya University. Indore, India. February 24–25. Buddhi, D., Sawhney, R.L., Seghal, P.N., Bansal, N.K. (1987). A simplification of the differential thermal analysis method to determine the latent heat of fusion of phase change materials. *J Physics D Applied Physics* 20:1601–1605.
30. Buddhi, D., Sharma, S.D. (1999). Measurements of transmittance of solar radiation through stearic acid: a latent heat storage material. *Energy Conversion and Management* 40:1979–1984.
31. Buddhi, D., Sharma, S.D. (2000). Thermal performance studies of a latent heat storage unit for night cooking. TERRASTOCAL. *Proc. Of 8th International Conference on Thermal Energy Storage*. Stuttgart, Germany 2:615–618.
32. Buddhi, D., Sharma, S.D., Sharma, A. (2003). Thermal performance evaluation of a latent heat storage unit for late evening cooking in a solar cooker having three reflectors. *Energy Conversion and Management* 44:809–817.
33. Bukovec, N., Bukovec, P., Arbanas, V. (1989). TG and DSC investigation of $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$ a phase change material. *Thermochemica Acta* 148: 281–288.
34. Bulkin, S.G., Vyrlan, P.M., Pleshka, M.S. (1988). Mathematical model of a solar assisted heat pump system with solar absorbers and two thermal storage tanks. *Applied Solar Energy* 21:41.
35. Bushnell, D.I. (1988). Performance studies of solar energy storing heat exchanger. *Solar Energy* 41(6): 503–12.

36. Cabeza, L.F., Illa, J., Roca, J., Badia, F., Mehling, H., Hiebler, S., Ziegler, F. (2001a). Immersion corrosion tests on metal-salt hydrate pairs used for latent heat storage in the 32 to 36 °C temperature range. *Mater Corros* 52: 140–146.
37. Cabeza, L.F., Illa, J., Roca, J., Badia, F., Mehling, H., Hiebler, S., Ziegler, F. (2001b). Middle term immersion corrosion tests on metal-salt hydrate pairs used for latent heat storage in the 32 to 36 °C temperature range. *Mater Corros*. 52: 748–754.
38. Cabeza, L.F., Mehling, H., Hiebler, S. (2005). Immersion corrosion tests on metal-salt hydrate pairs used for latent heat storage in the 48 to 58 °C temperature range. *Mater Corros*. 56(1): 33–38.
39. Cabeza, L.F., Roca, J., Nogues, M., Zalba, B., Marin, J.M. (2002). Transportation and conservation of temperature sensitive materials with phase change materials: state of the art. IEA ECES IA Annex 17. 2nd Workshop. Ljubljana, Slovenia. April 4–5.
39. Canbazoglu, S., Sahinaslan, A., Ekmekyapar, A., Aksoy, Y.G., Akarsu, F. (2005). Enhancement of solar thermal energy storage performance using sodium thiosulfate pentahydrate of a conventional solar water-heating system. *Energy and Buildings*. 37(3): 235–242.
40. Cantor, S. (1978). Applications of differential scanning calorimetry to the study of thermal energy storage. *Thermochemica Acta* 26(1–3): 39–47.
41. Chaurasia, P.B.L. (1986). Study of solar energy storage in paraffin wax storage system up to two night duration. *India Energy Abstract* 5(3–4): 14.
42. Chen, S.L. (1991a). An experimental investigation of cold storage in packed capsules with solidification. *Int J Exp Heat Transfer* 4: 263–280.
43. Chen, S.L., Chen, C.L., Tin, C.C., Lee, T.S., Ke, M.C. (2000). An experimental investigation of cold storage in an encapsulated thermal storage tank. *Experimental Thermal and Fluid Science* 23(3–4): 133–144.
44. Chen, S.L., Wang, P.P., Lee, T.S. (1991b). An experimental investigation of nucleation probability of supercooled water inside cylindrical capsules. *Experimental Thermal and Fluid Science* 18: 299–306.
45. Chen, S.L., Yue, J.S. (1991c). A simplified analysis for cold storage in porous capsules with solidification. *ASME J Energy Resources Technology* 113: 108–116.
46. Chen, S.L., Yue, Y.S. (1991d). Thermal performance of cool storage in packed capsules for air conditioning. *Heat Recovery System CHP* 11(6): 551–561.
47. Choi, J.C., Kim, S.D. (1992). Heat-transfer characteristics of a latent heat storage system using $MgCl_2 \cdot 6H_2O$. *Energy* 17(8): 1153–64.
48. Collier, R.K., Grimmer, D.P. (1979). The experimental evaluation of phase change material building walls using small passive test boxes. *Proceedings of the 3rd National Passive Solar Conference*. San Jose, CA. January 11.
49. Colvin, D.P. (1999). Advances in heat and mass transfer in biotechnology. *ASME HTD* 44: 199.
50. Colvin, D.P., Bryant, Y.G. (1988). Protective clothing containing encapsulated phase change materials. *Proceedings of ASME International Mechanical Engineering Congress and Exposition*. Anaheim, CA: 23–32.
50. Costa, M., Buddhi, D., Oliva, A. (1998). Numerical Simulation of a latent heat thermal energy storage system with enhanced heat conduction. *Energy Conversion and Management* 39:319–30.
51. Dietz, D. (1984). Thermal performance of a heat storage module using calcium chloride hexahydrate. *Trans ASME* 106: 106–111.
52. Dorgan, C.E., Elleson, J.S. (1993). Design guide for cool thermal storage. *American Society of Heating, Refrigerating and Air Conditioning Engineers, Inc.*, Atlanta, GA.
53. Domanski, R., El-Sayed, O.A., Jaworski, M. (1994). Experimental study for the melting of PCM inside concentric horizontal cylindrical annuli. *Proceedings of 6th International Conference on Thermal Energy Storage*. Espoo, Finland: 503–511.
54. Domanski, R., El-Senai, A.A., Jaworski, M. (1995). Cooking during off-sunshine hours using as storage media. *Energy* 20(7): 607–616.
55. Dunn, J.G., Smith, H.G., Willix, R.L. (1989). The supercooling of acetamide. *Thermochemica Acta* 80: 343–353.
56. Eftekhari, J., Sheikh, A.H., Lou, D.Y.S. (1984). Heat transfer enhancement in a paraffin wax thermal storage system. *J Solar Energy Eng* 106: 299–306.
57. El-Dessouky, H., Al-Juwayhel, F. (1997). Effectiveness of a thermal energy storage system using phase change materials. *Energy Conversion and Management* 38: 601–617.
58. El-Kassaby, M.M., Ahmed, A.E. (1993). Modeling of a heat exchanger utilizing a phase change material for short-term storage. *Renewable Energy* 3(8):857–865.
59. Elder, J.P. (1980). Thermal energy storage materials - a DSC study. *Thermochemica Acta* 36(1):67–77.
60. Enibe, S.O. (2002). Performance of a natural circulation solar air heating system with phase change material energy storage. *Renewable Energy* 27: 69–86.
61. Enibe, S.O. (2003). thermal analysis of a natural circulation solar air heater with phase change material energy storage. *Renewable Energy* 28: 2269–2299.
62. Erk, H.F., Dudukovic, M.P. (1996). Phase-change heat regenerators: modeling and experimental studies. *Aiche* 42(3): 791–808.
63. Ettouney, H.M., Alatiqi, I., Al-Sahali, M., Al-Ali, S.A. (2004). Heat transfer enhancement by metal screens and metal spheres in phase change energy storage systems. *Renewable Energy* 29: 841–860.
64. Farid, M.M., Hamad, F.A., Abu-Arabi, M. (1988). Phase change cool storage using dimethyl-sulfoxide. *Energy Conversion and Management* 39 (8): 819–826.
64. Farid, M.M., Husian, R.M. (1990). An electrical storage heater using the phase change method of heat storage. *Energy Conversion and Management* 30(3): 219–230.
65. Farid, M.M., Khudhair, A., Razacksak, Al-Hakkaj, S. (2004). A review of phase change energy storage: materials and applications. *Energy Conversion and Management* 45: 1597–1615.
66. Farid, M.M., Yacoub, K. (1989). Performance of direct contact latent heat storage unit. *Solar Energy* 43(4): 237–51.
67. Fath Hassan, E.S. (1995). Thermal performance of a simple design solar air heater with built-in thermal energy storage system. *Energy Conversion and Management* 36(10): 989–997.
68. Fath, H.E.S. (1991). Heat exchanger performance for latent heat thermal energy storage system. *Energy Conversion and Management* 31(2): 149–155.
69. Feldman, D., Banu, D. (1996). DSC analysis for the evaluation of an energy storing wallboard. *Thermochemica Acta* 272: 243–251.
70. Feldman, D., Banu, D., Hawes, D. (1995). Development

and application of organic phase change mixtures in thermal storage gypsum wallboard. *Solar Energy Materials and Solar Cells* 44:147–157.

71. Feldman, J.E. (1970). U.S. Patent. 3,536,059.

72. Fernanda, G.P. (1988). Salt hydrates used for latent heat storage: corrosion metals and reliability of thermal performance. *Solar Energy* 41(2): 193–197.

73. Flaherty, B. (1971). Characterisation of waxes by differential scanning calorimeter. *J Appl Chem Biotechnology*. 21: 144.

74. Font, J., Muntasell, J., Cardoner, F. (1994). Preliminary study of a heat storage unit using a solid- solid transition. *Solar Energy Materials and Solar Cells* 33 (2): 169–176. Fraunhofer. (2002). ISE www.ise.fhg.de.

75. Fukai, J., Hamada, Y., Morozumi, Y., Miyatake, O. (2002). Improvement of thermal characteristics of latent heat thermal energy storage units using carbon-fiber brushes: experiments and modeling. *Int J Heat and Mass Transfer* 46: 4513–4525.

76. Gaorvon, K., Scroder, J. (1977). Properties of some salt hydrates for latent heat storage. *Energy Research* 1: 351.

77. Garg, H.P., Mullick, S.C., Bhargava, A.K. (1985). *Solar Thermal Energy Storage*. Dordrecht, Holland: D. Reidel Publishing Co.

78. Ghoneim, A.A. (1989). Comparisons of theoretical models of phase change and sensible heat storage for air and water based solar heating systems. *Solar Energy* 42(3): 209–220.

79. Ghoneim, A.A., Klein, S.A., Duffie, J.A. (1991). Analysis of collector – storage building walls using phase change materials. *Solar Energy* 47 (1): 237–242.

80. Giavarini, C., Pochetti, F. (1972). Characterization of petroleum products by dsc analysis. *J Thermal Analysis* 5: 83–94.

81. Gibbs, B.M., Hasnain, S.M. (1995). DSC study of technical grade phase change heat storage materials for solar heating applications. *Proceedings of the 1995 ASME/JSME/ISEI International Solar Energy Conference*, Part 2. Lahaina, Maui, HI. March 19–24.

82. Gong, Z.X., Mujumdar, A.S. (1997). Finite element analysis of cyclic heat transfer in a shell-and- tube latent heat energy storage exchanger. *Applied Thermal Engineering* 17(6): 583–591.

83. Groll, M., Brost, O., Heine, D. (1990). Corrosion of steels in contact with salt eutectics as latent heat storage materials: influence of water and other impurities. *Heat Recovery Systems & CHP* 10:567–72.

84. Gu, Z., Liu, H., Li, Y. (2004). Thermal energy recovery heat recovery system calculation and phase change material development. *Applied Thermal Engineering* 24: 2511–2426.

85. Gustafsson, M., Bo He, Seterwall, F. (1998). Paraffin waxes and their mixture as phase change materials (PCMs) for cool storage in district cooling system. IEA Annex 10, 45–56, Adana, Turkey. April 16–17.

86. Hadjieva, M., Kanev, S., Argirov, J. (1992). Thermophysical properties of some paraffins applicable to thermal energy storage. *Solar Energy Materials and Solar Cells* 27:181–187.

87. Hafner, B., Schwarzer, K. (1999). Improvement of the heat transfer in a phase-change-material storage. *Proceedings of the IEA ECES IA Annex 10. 4th Workshop*. Benedikbauern, Germany. October 28–29.

88. Hale, D.V., Hoover, M.J., O'Neill, M.J. (1971). Phase

Change Materials Hand Book, Report no. HREC- 5183-2LMSC-HREC D225138. NASA. Marshal Space Flight Center. Alabama.

89. Hasan, A. (1994). Thermal energy storage system with stearic acid as phase change material. *Energy Conversion and Management* 35(10): 843–856.

90. Hasan, A., Sayigh, A.A. (1994). Some fatty acids as phase change thermal energy storage materials. *Renewable Energy* 4(1): 69–76.

91. Hasnain, S. (1998). Review on sustainable thermal energy storage technologies, part I: heat storage materials and techniques. *Energy Conservation and Management* 39: 1127–1138.

92. Hatano, M., Asano, Y. (1995). A study on prediction control of latent floor-heating storage system using off-peak electricity equipped in a school building. *Journal of Architectural Planning Environmental Engineering* 469 (3): 25–33.

93. Hawlader, M.N., Uddin, M.S., Zhu, H.J. (2002). Encapsulated phase change materials for thermal energy storage: experiments and simulation. *International Journal of Energy Research* 26:159–71.

94. He, B., Setterwall, F. (2001). Technical grade paraffin waxes as phase change materials for cool thermal storage and cool storage systems capital cost estimation. *Energy Conversion and Management* 43: 1709–1723.

95. He, Q., Zhang, W. (2001). A study on latent heat storage exchangers with the high-temperature phase-change material. *International Journal of Energy Research* 25: 331–241.

96. Heine, D. (1981). The Chemical compatibility of construction materials with latent heat storage materials. *Proceedings of the International Conference on Energy Storage*. Brighton, UK.

Herrick, C.S. (1978). Thermal energy storage subsystem for solar heating and cooling applications. 3rd Annual Energy Storage Concentrator's Information Exchange Meeting. Springfield, VA.

97. Hiran, S., Suwondo, A., Mansoori, G. (1994). Characterization of alkanes and paraffin waxes for application as phase change energy storage medium. *Energy Sources* 16: 117–128.

98. Hong, H., Kim, S.K., Kim, Y.S. (2004). Accuracy improvement of t-history method for measuring heat of fusion of various materials. *International Journal of Refrigeration* 27: 360–366.

Hoogendoorn, C.J., Bart, C.C.J. (1992). Performance and modeling of latent heat stores. *Solar Energy* 48: 53–58.

99. Huang, M. (2002). The application of CFD to predict the thermal performance of phase change materials for the control of photovoltaic cell temperature in buildings. Ph.D. Thesis. University of Ulster, UK.

100. Huang, M., Eames, P.C., Norton, B. (2000). The application of computational fluid dynamics to predict the performance of phase change materials for control of photovoltaic cell temperature in buildings. *Proceedings of VI World Renewable Energy Congress*. Brighton, UK: 2123–2126.

101. Huang, M., Eames, P.C., Norton, B. (2001). An experimental study into the application of phase change materials to limit the temperature rise in build integrated photovoltaic systems. *Proceedings of Renewable Energy In Maritime Island Climates*. Belfast, UK: 143–150.

102. Huang, M.J., Eames, P.C., Norton, B. (2004). Thermal regulation of building-integrated photovoltaics using phase

change materials. *International Journal of Heat and Mass Transfer* 47: 2715–2733.

103. Hung, B.K., Abrams, C.F., Coasts, L.L., Bowers, C.G. (1975). Development of greenhouse bulk drying systems for solar energy utilization and planted mechanization. *ASHARE*: 75–1018.

104. Hung, B.K., Toksoy, M. (1983). Design and analysis of greenhouse solar system in agricultural production. *Energy in Agriculture* 2: 115–136.

105. Inaba, H., Tu, P. (1997a). Evaluation of thermophysical characteristics on shape-stabilized paraffin as a solid–liquid phase change material. *Heat Mass Transfer* 32: 307–312.

106. Inaba, H., Sato, K. (1997b). Latent cold heat energy storage characteristics by means of direct contact freezing between oil droplets and cold water solution. *International Journal of Heat Mass Transfer* 40 (13): 3189–3200.

107. Ismail, K.A.R., Alves, C.L.F. (1986). Analysis of shell-and-tube PCM storage system. Paper No. FM-10. *Proc 8th Int Heat Transfer Conference*. San Francisco CA.

108. Jaffrin, A., Cadier, P. (1982). Latent heat applied to horticulture–la baronne solar greenhouse. *Solar Energy* 38(4): 313–321.

109. Jaffrin, A., Cadier, P., Venard, M. (1987). La baronne solar greenhouse of CREAT-CNRS. In REUR Technical Series I. *Greenhouse Heating with Solar Energy*. CNRE: 192–194.

110. Jahns, E. (1999). Microencapsulated phase change materials. *Proceedings of the 4th IEA ECES IEA Annex 10 Workshop*. Benediktbeuern, Germany.

111. John, T., David, E., David, R. (2000). A novel ventilation system for reducing air conditioning in buildings: testing and theoretical modeling. *Applied Thermal Engg* 20: 1019–37.

112. Jurinak, J.J., Abdel Khalik, S.I. (1978). Properties optimization for phase change energy storage in air based solar heating systems. *Solar Energy* 21(5): 377–383.

113. Jurinak, J.J., Abdel Khalik, S.I. (1979). Sizing phase change energy storage units for air based solar heating systems. *Solar Energy* 22(4): 355–359.

114. Kamimoto, M., Abe, Y., Sawata, A., Tani, T., Ozawa, T. (1986a). Latent thermal storage unit using form-stable polyethylene part ii: performance of the storage unit. *ASME Journal of Solar Energy Engineering* 108: 287–290.

115. Kamimoto, M., Abe, Y., Kanari, K., Swata, S., Tani, T., Ozawa, T. (1986b). Heat transfer in latent heat thermal storage units using pentarythritol slurry thermal energy storage. World Congress of Chemical Engineering. Tokyo, Japan. September 21–24.

116. Kauranen, P., Peippo, K., Lund, P.D. (1991). An organic PCM storage system with adjustable melting temperature. *Solar Energy* 46: 275–278.

117. Kaygusuz, K. (1995a). Performance of solar assisted heat pump system. *Applied Energy* 51(2): 93–109.

118. Kaygusuz, K. (1995b). Experimental and theoretical investigations of latent heat storage for water based solar heating system. *Energy Conversion and Management* 36(5): 315–323.

119. Kaygusuz, K. (1999). The viability of thermal energy storage. *Energy Sources* 21: 745–755. Kaygusuz, K., Comakli, O., Ayhan, T. (1991). Solar assisted heat pump systems and energy storage. *Solar Energy* 27: 383.

120. Kern, M., Aldrich, R.A. (1979). Phase change energy storage in a greenhouse solar heating system. Paper Presented at the Summer Meeting of ASAE and CSAE. University of

Manitoba, Winnipeg, Canada. June 24–27.

121. Khan, M.A., Rohatgi, P.K. (1994). Numerical solution to a moving boundary problem in a composite medium. *Numer Heat Transfer* 25: 209–221.

122. Khateeb, S.A., Farid, M.M., Selman, J.R., Al-Hallaj, S. (2004). Design and simulation of a lithiumion battery with a phase change material thermal management system for an electric scooter. *Journal of Power Sources* 128: 292–307.

123. Khudhair, A., Farid, M.M., Ozkan, N., Chen, J. (2003). Thermal performance and mechanical testing of gypsum wallboards with latent heat storage. *Proceedings of Annex 17, Advanced Thermal Energy Storage through Phase Change Materials and Chemical Reactions Feasibility Studies and Demonstration Projects*. Indore, India. (www.fskab.com/Annex17).

124. Kimura, H., Kai, J. (1984). Phase change stability of $\text{CaCl}_2 \cdot 6\text{H}_2\text{O}$. *Solar Energy* 33: 557–63. *Kinds of Chemical Products in Japan*. (1988). Kagaku-Kougyou-Nippou-Sha (in Japanese). Chemical Industry Daily Report Corp., ISBN 4-87362-267-4, Tokyo, Japan.

125. Klein, S.A., Beckman, W.A. (1979). A general design method for closed loop solar energy systems. *Solar Energy* 22(3): 269–282.

126. Koizumi, H. (2004). Time and spatial heat transfer performance around an isothermally heated sphere placed in a uniform, downwardly directed flow (in relation to the enhancement of latent heat storage rate in a spherical capsule). *Applied Thermal Engineering* 27(17/18): 2583–2600.

127. Kondepudi, S., Somasundaram, S., Anand, N.K. (1988). A simplified model for the analysis of a phase-change material-based thermal energy storage system. *Heat Recovery System CHP* 8(3): 247–254.

128. Koschenz, M., Lehmann, B. (2004). Development of a thermally activated ceiling panel with pcm for application in lightweight and retrofitted buildings. *Energy and Buildings* 36: 567–578.

129. Kurklu, A. (1998). Energy storage applications in greenhouse by means of phase change materials (pcms): a review. *Renewable Energy* 13 (1): 89–103.

130. Kurklu, A., O' Zmerzi, A., Bilgin, S. (2002). Thermal performance of a water- phase change material solar collector. *Renewable Energy* 26: 391–399.

131. Kurklu, A., Ozmerzi, A., Wheldon, A.E., Hadley, P. (1996). Utilization of a phase change material (PCM) for the reduction of peak temperatures in a model greenhouse. Paper Presented at Agritech

132. International Workshop on Greenhouse Technologies for Mild Climates. Bet-Dagan. Acta Horticulturae, Israel. May 12–16.

133. Kurklu, A., Wheldon, A.E., Hadley, P. (1997). Use of a phase change material (PCM) for frost prevention in a model greenhouse. *J Enging Sci Univ Pamukkale*

134. Lacroix, M. (1993a). Numerical simulation of a shell- and -tube latent thermal energy storage unit. *Solar Energy* 50 (4): 357–367.

135. Lacroix, M. (1993b). Study of the heat transfer behavior of a latent heat thermal energy storage unit with a finned tube. *Int J Heat Mass Transfer* 36: 2083–2092.

136. Lane, G. A. (1983). *Solar Heat Storage: Latent Heat Materials*, Vol. I. Boca Raton, Florida: CRC Press.

137. Lane, G.A. (1975). Heat of fusion systems for solar energy storage. *Proc Workshop Solar Energy Storage*

Subsystems for the Heating and Cooling of Buildings. Charlottesville, VA: 43–55.

138. Lane, G.A. (1980). Low temperature heat storage with phase change materials. *International Journal of Ambient Energy* 1: 155–68.

139. Lane, G.A. (1989). Phase Change Thermal Storage Materials. In: *Hand Book of Thermal Design*. In: Guyer, C., ed. McGraw Hill Book Co.

140. Laybourn, D.R. (1988). Thermal energy storage with encapsulated ice. *ASHRAE Trans* 94 (1): 1971–1988.

141. Lecomte, D., Mayer, D. (1985). Design method for sizing a latent heat store/ heat exchanger in a thermal system. *Applied Energy* 21(1): 55–78.

142. Lee, C.H, Choi, H.K. (1998). Crystalline morphology in high density polyethylene/paraffin blend for thermal energy storage. *Polym Composites* 19 (6): 704–708.

143. Leoni, N., Amon, C.H. (1997). Transient thermal design of wearable computers with embedded electronics using phase change materials. *ASME HTD* 437(5): 241–250.

144. Levav, N., Zamir, N. (1987). phase change materials for heat storage in greenhouse. In: *REUR Technical Series L: Greenhouse Heating with Solar Energy*. CNRE: 163–166.

145. Li, W., Zhang, D., Zhang, T., Wang, T., Ruan, D., Xing, D., Li, H. (1999). Study of solid-solid phase change of $(N-C_nH_{2n+1}NH_3)_2MCl_4$ for thermal energy storage. *Thermochemica Acta* 326: 183–186.

Lin, K., Zhang, Y., Xu, X., Di, H., Yang, R., Qin, P. (2004). Modeling and simulation of under- floor electric heating system with shape-stabilized PCM plates. *Building and Environment* 39:1427–1434.

146. Liu, Z., Chung, D.D.L. (2001). Calorimetric evaluation of phase change materials use as thermal interface materials. *Thermochemica Acta* 366: 135–147.

147. Maccracken, C.D. (1981). PCM Bulk Storage. *Proc Int Conf on Energy Storage*. Brightiton, U.K.: 159–165.

Manz. (1997). TIM-PCM external wall system for solar space heating and daylighting. *Solar Energy* 61(6): 369–379.

148. Marin, J.M., Zalba, B., Cabeza, L.F., Mehling, H. (2003). Determination of enthalpy–temperature curves of phase change materials with the temperature-history method: improvement to temperature dependent properties. *Meas Sci Technol* 14: 184–189.

149. Marinkovi, M., Nikoli, R., Savovi, J., Gadzuri, S., Zsigrai, I. (1998). Thermochromic complex compounds in phase change materials: possible application in an agricultural greenhouse. *Solar Energy Materials and Solar Cells* 51(3–4): 401–411.

150. Marks, S. (1980). An investigation of the thermal energy storage capacity of glauber's salt with respect to thermal cycling. *Solar Energy* 25: 255–8.

151. Mehling, H., Hiebler, S., Ziegler, F. (1999). Latent heat storage using a PCM-graphite composite material: advantages and potential applications. *Proceedings of the 4th Workshop of IEA ECES IA Annex 10*. Bendiktbeuern, Germany. October 28–29.

152. Mehmet, E. (2000). Thermal Performance of a Solar-Aided Latent Heat Store Used For Space Heating by Heat Pump. *Solar Energy* 69(1): 15–25.

153. Merritt, R.H., Ting, K.C. (1995). Morphological responses of bedding plants to three greenhouse temperature regimes. *Scientia Horticulturae* 60 (3–4): 313–324.

154. Mitsubishi Chemical Co. Ltd. 2nd November 2004. <http://www.mitsubishi-chem-eng.co.jp/stl/>

index.htm

155. Morcos, V.H. (1990). Investigation of a latent heat thermal energy storage system. *Solar Wind Technol* 7: 197–202.

156. Mullick, S.C., Kandpal, T.C., Saxena, A.K. (1987). Thermal Test procedure for box type solar cookers. *Solar Energy* 39(4): 353–360.

157. Mulligan, J.C., Colvin, D.P., Bryant, Y.G. (1996). Microencapsulated phase-change material suspensions for heat transfer in spacecraft thermal systems. *J Spacecraft and Rockets* 33: 278–284. Nagano, K., Mochida, T., Takeda, S., Domanski, D., Rebow, M. (2003). Thermal performance of maganese (ii) nitrate hexahydrate as a phase change materials for cooling systems. *Applied Thermal Engineering* 23(2): 229–243.

158. Nagano, K., Takeda, S., Mochida, T., Shimakura, K. (2004a). Thermal characteristics of a direct heat exchange system between granules with phase change material and air. *Applied Thermal Engineering* 24: 2131–2144.

159. Nagano, K., Ogawa, K., Mochida, T., Hayashi, K., Ogoshi, H. (2004b). Thermal characteristics of magnesium nitrate hexahydrate and magnesium chloride hexahydrate mixture as a phase change material for effective utilization of urban waste heat. *Applied Thermal Engineering* 24: 221–232.

160. Naim, M.M., Kawib, M.M.A.E. (2002). Non-conventional solar stills part 2. Non-conventional solar stills with energy storage element. *Desalination* 153: 71–80.

161. Neeper, D.A. (2000). Thermal dynamics of wallboard with latent heat storage. *Solar Energy* 68 (5): 393–403.

162. Nishina, H., Takakura, T. (1984). Greenhouse heating by means of latent heat storage units (Energy in Protected Cultivation III). *Acta Hort.* 148: 751–754.

163. Olsson, L. (2004). Cooling of newborn baby with PCM. IEA ECES IA Annex 17 6th Workshop. Arvika, Sweden. (www.fskab.com/Annex17)

164. Omer, S.A., Riffat, S.B., Ma, X. (2001). Experimental investigation of a thermoelectric refrigeration system employing a phase change material integrated with thermal diode (thermosyphons). *Renewable Energy* 21: 1265–1271.

Ona, E.P., Zhang, X., Kyawk, Watanabe F., Matsuda, H., Kakiuchi, H., Yabe, M., Chihara, S. (2001).

165. Relaxation of supercooling of erythritol for latent heat storage. *J Chem Eng Japan* 34(3): 376–382. Padmanabhan, P.V., Murthy, M.V. (1986). Outward phase change in a cylindrical annulus with axial fins on the inner tube. *Int J Heat Mass Transfer* 29: 1855–68.

166. Pal, D., Joshi, Y. (1996). Application of phase change materials for passive thermal control of plastic quad flat packages: a computational study. *Numerical Heat Transfer Part A* 30: 19–34.

167. Pal, D., Joshi, Y. (1997). Application of phase change materials to thermal control of electronic modules: a computation study. *Trans ASME* 119: 40–50.

168. Pillai, K.K., Brinkwarth, B.J. (1976). The storage of low grade thermal energy using phase change materials. *Applied Energy* 2: 205–216.

169. Porisino, F.G. (1988). Salt Hydrates used for latent heat storage corrosion of metals and reliability of thermal performance. *Solar Energy* 41: 193–7.

170. Prakesh, J., Garg, H.P., Datta, G. (1985). A solar water heater with a builtin latent heat storage. *Energy Conversion and Management* 25(1): 51–56.

171. Py, X., Olives, S., Mauran, S. (2001). Paraffin/porous

graphite matrix composite as a high and constant power thermal storage material. *Int J Heat Mass Transfer* 44: 2727–37.

172. Qarnia, H. El., Lacroix, M., Mercadier, Y. (2001). Use of a phase change material to prevent frosting in a compact cross-flow air exchanger. *Energy Conversion and Management* 42: 1277–1296.

173. Ramadan, M., Aboul-Enein, S., El-Sebaei, A. (1987). A model of an improved low cost indoor solar cooker in Tanta. *Solar & Wind Technology* 5(4): 387–393.

174. Revankar, S. (2001). Purdue University News Bulletin. June8.(news.uns.purdue.edu/html4ever/010607.Revankar.solar.html.)

175. Richardson, M.J. (1993). The derivation of thermodynamic properties by DSC: free energy curves and phase stability. *Thermochemica Acta* 36(1): 67–77.

176. Royon, L., Guiffant, G., Flaud, P. (1997). Investigation of heat transfer in a polymeric phase change material for low level heat. *Energy Conversion and Management* 38: 517–24.

177. Ryu, H.W., Hong, S.A., Shin, B.C., Kim, S.D. (1991). Heat transfer characteristics of cool-thermal storage systems. *Energy* 16 (4): 727–737.

178. Sagara, K., Hisano, K., Terashima, T. (1994). Performance of latent thermal storage for solar heating system. Mie University, Japan. Mie Academic Press B: 83–88.

179. Saitoh, T., Hirose, K. (1986). High-performance phase-change thermal energy storage using spherical capsules. *Chem Eng Commun* 41: 39–58.

180. Salyer, I.O. (1999). Phase change materials incorporated throughout the structure of polymer fibers. US Patent 5,885,475.

181. Salyer, I.O., Sircar, A.K., Chartoff, R.P. (1986). Analysis of crystalline paraffinic hydrocarbons for thermal energy storage by differential scanning calorimetry: part 1, pure hydrocarbons. 15th North American Thermal Analysis Society Conference. Cincinnati. OH.

182. Santamouris, M., Balaras, C.A., Dascalaki, E., Vallindras, M. (1994). passive solar agricultural greenhouses: a worldwide classification and evaluation of technologies and systems used for heating purposes. *Solar Energy* 53 (5): 411 - 426.

183. Sari, A. (2004). Form-stable paraffin/high density polyethylene composites as solid–liquid phase change material for thermal energy storage: preparation and thermal properties. *Energy Conversion and Management* 45: 2033-2042.

184. Sari, A., Kaygusuz, K. (2000). Energy and exergy calculations of latent heat storage systems. *Energy Sources* 22: 117-126.

185. Sari, A., Kaygusuz, K. (2001). Thermal energy storage system using stearic acid as a phase change material. *Solar Energy* 71(6): 365 - 376.

186. Sari, A., Kaygusuz, K. (2002). Thermal performance of a eutectic mixture of lauric and stearic acids as PCM encapsulated in the annulus of two concentric pipes. *Solar Energy* 72(6): 493-504.

187. Sari, A., Kaygusuz, K. (2003a). Some fatty acids used for latent heat storage: thermal stability and corrosion of metals with respect to thermal cycling. *Renewable Energy* 28: 939-48.

188. Sari, A. (2003b). Thermal reliability test of some fatty acids as PCMs used for solar thermal latent storage applications. *Energy Conversion and Management* 44: 2277 - 87.

189. Saxena, S., Subrahmaniyam, S., Sarkar, M.K. (1982). A preliminary model for phase change thermal energy storage in a shell and tube heat exchanger. *Solar Energy* 29(3): 257-263.

190. Sharma, A., Sharma, S.D., Buddhi, D. (2002). Accelerated thermal cycle test of acetamide, stearic acid and paraffin wax for solar thermal latent heat storage applications. *Energy Conversion and Management* 43: 1923-1930.

191. Sharma, A., Sharma, S.D., Buddhi, D., Sawhney, R.L. (2001). Thermal cycle test of urea for latent heat storage applications. *Int J Energy Research* 25: 465-468.

192. Sharma, S.D. (1999). Study of thermal energy storage in phase change materials for low temperature solar applications. Ph.D. Dissertation, Devi Ahilya University, Indore, India.

193. Sharma, S.D., Buddhi, D., Sawhney, R.L. (1998). Accelerated thermal cycle tests of industrial grade phase change materials. Proc. National Solar Energy Convention-97: Towards Commercialization of Clean Energy. Chennai. India. Anna University: 73-77.

194. Sharma, S.D., Buddhi, D., Sawhney, R.L. (1999). Accelerated thermal cycle test of latent heat storage materials. *Solar Energy* 66: 483-490.

195. Sharma, S.D., Buddhi, D., Sawhney, R.L., Sharma, A. (2000). Design development and performance evaluation of latent heat storage unit for evening cooking in a solar cooker. *Energy Conversion and Management* 41: 1497–1508.

196. Sharma, S.D., Iwata, T., Kitano, H., Sagara, K. (2004). Thermal performance of a solar cooker based on evacuated tube solar collector with a PCM storage unit. *Solar Energy* (in press).

197. Shibutani, S. (2002). PCM Micro-capsule slurry thermal storage system for cooling in narita airport. 3rd Workshop of the IEA ECES IA Annex. 17 Tokyo, Japan. September 30 – October 2. Shitzer, A., Levy, M. (1983). Trans ASME. *J Sol Energy Engineering* 105: 200.

198. Shumitomo Chemical Co. Ltd. (2004) November 2. <http://www.sumitomo-chem.jp/english/division/petro.html>

Siegel, R. (1977). Solidification of low conductivity material containing dispersed high conductivity particles. *Int J Heat Mass Transfer* 20: 1087–1089.

199. Solmar, A., Persson, J., Loyd, D. (1989). Field testing and simulation of a cool storage at a ware-house. 9th International Congress on Energy and Environment. Miami, USA. December 11–13. Song, H-Kasp. (1988). Utilization of latent heat storage materials for the high concentrated thermal energy storage. Report No. 1988.5 - 1990.5.

200. Sparrow, E.M., Larsen, E.D., Ramsey, J.W. (1981). Freezing on a finned tube for either conduction controlled or natural convection controlled heat transfer. *Int J Heat Mass Transfer* 24: 273–284.

201. Stovall, T.K., Arimilli, R.V. (1988). Transient thermal analysis of three fast-changing latent heat storage configuration for a space-based power system. *Proceedings of the 23rd Inter Society Energy Conversion Engineering Conference*. Denver, Colorado: 71–177.

202. Strith, U., Novak, P. (2002). Thermal storage of solar energy in the wall for building ventilation. IEA, ECES IA Annex 17. *Advanced Thermal Energy Storage Techniques - Feasibility Studies and Demonstration Projects 2nd Workshop*. Ljubljana, Slovenia.

203. Swet, C.J. (1980). Phase change storage in passive solar architecture. *Proc 5th National Passive Solar Conference*. Amherst, Massachusetts.

204. Takahashi, Y., Neigishi, A., Abe, Y., Tanaka, K., Kamimoto, M. (1991). Thermoanalytical investigation of fluoride composites for latent thermal storage.

Thermochemica Acta 183: 299–311.

205. Takakura, T., Nishina, H. (1981). a solar greenhouse with phase change energy storage and a micro computer control system. *Acta Hort (Energy in Protected Cultivation)* 115: 583–590.
206. Takeda, S., Nagano, K., Mochida, T., Shimakura, K. (2004). Development of a ventilation system utilizing thermal energy storage for granules containing phase change materials. *Solar Energy* 77: 329–338.
207. Tan, F.L., Tso, C.P. (2004). Cooling of mobile electronics devices using phase change materials. *Applied Thermal Engineering* 24: 159–169.
208. Tanishita, I. (1970). Present situation of solar water heaters in Japan. Paper No. 2/73. *Int Solar Energy Society Conference*. Melbourne, Australia.
209. Tavaranan, S., Das, A., Aurora, P., Trelles, J.P. (2002). Design of a standalone portable solar powered thermoelectric vaccine refrigerator using phase change material as thermal backup. Solar Engineering Program, University of Massachusetts Lowell, MA.
210. Tayeb, A.M. (1993). A simulation model for a phase change energy storage system: experimental and verification. *Energy Conversion and Management* 34 (4): 243–250.
211. Telkes, M. (1959). Solar cooking ovens. *Solar Energy* 3(1): 1–11.
212. Telkes, M. (1974). Solar Energy Storage. *Am Soc Heat Refrig & Air Cond Engrs*: 38–44.
213. Telkes, M. (1975). Thermal storage for solar heating and cooling. *Proceedings of the workshop on solar energy storage subsystems for the heating and cooling of buildings*. Charlottesville, Virginia, USA.
214. Telkes, M. (1978). Trombe wall with phase change storage material. *Proceedings of the 2nd national passive solar conference*. Philadelphia, PA, USA.
215. Thulasi Das, T.C., Karmakar, S., Rao, D.P. (1994). Solar box cooker: part 1 modeling. *Solar Energy* 52(3): 265–272.
216. Ting, K.C., Giannakakas, P.N., Gilbert, S.G. (1987). Durability of latent heat storage tube sheets. *Solar Energy* 39(2): 79–85.
217. Tiwari, G.N., Rai, S.N., Santram, Singh M. (1988). Performance prediction of PCCM collection- cum-storage water heater: quasi-steady state solution. *Energy Conversion and Management* 28 (3): 219–223.
218. Tong, X., Khan, J., Amin, M.R. (1996). Enhancement of heat transfer by inserting a metal matrix into a phase change material. *Num Heat Trans Part A Applied* 30(2): 125–41.
219. Trelles, J.P., Duffy, J.P. (2003). Numerical simulation of porous latent heat thermal energy storage for thermoelectric cooling. *Applied Thermal Engineering* 23: 1647–1664.
220. Turpenny, J.R., Etheridge, D.W., Reay, D.A. (2000). Novel ventilation cooling system for reducing air conditioning in building part1 testing and theoretical modeling. *Applied Thermal Engineering* 20: 1019–1037.
221. Ulfvengren, R. (2004). Will PCM help athletes in the Olympic games in Athens 2004? IEA ECES IA Annex 17 6th Workshop. Arvika, Sweden. (www.fskab.com/Annex17).
222. Vakilaltojjar, S.M., Saman, W. (2001). Analysis and modeling of a phase change storage system for air conditioning applications. *Applied Thermal Engineering* 21: 249–263.
223. Vasiliev, L.L., Burak, V.S., Kulakov, A.G., Mishkinis, D.A., Bohan, P.V. (2000). Latent heat storage modules for preheating internal combustion engines: application to a bus petrol engine. *Applied Thermal Eng.* 20: 913–923.
224. Velraj, R., Seeniraj, B., Hafner, B., Faber, C., Schwarzer, K. (1998). Heat transfer enhancement in a latent heat storage system. *Solar Energy* 65: 171–180.
225. Velraj, R., Seeniraj, R.V., Hafner, B., Faber, C., Schwarzer, K. (1997). Experimental analysis and numerical modeling of inward solidification on a finned vertical tube for latent heat storage unit. *Solar Energy* 60(5): 281–290.
226. Visser, H. (1986). Energy storage in phase-change materials-development of a component model compatible with TRNSYS. Final Report. Contract No. 2462-84-09 EI) ISPNL. Delft Univ. of Technology, Department of Applied Physics, Delft.
227. Wada, T., Yamamoto, R., Matsuo, Y. (1984). Heat storage capacity of sodium acetate trihydrate during thermal cycling. *Solar Energy* 33(3-4): 373–375.
228. Wang, X., Lu, E., Lin, W., Liu, T., Shi, Z., Tang, R., Wang, C. (2000). Heat storage performance of the binary systems neopentyl glycol/pentaerythritol and neopentyl glycol/trihydroxy menthyl-aminomethane as solid phase change materials. *Energy Conservation and Management* 41:129-134.
229. Watanbe, T., Kakikuchi, H., Kanzawa, A. (1993). Enhancement of charging and discharging rates in a latent heat storage system by use of pcm with different melting temperatures. *Heat Recov Syst CHP* 13(1): 57- 66.
230. Weindladerw; Beck, A., Fricke, J. (2004). PCM-facade-panel for day lighting and room heating. *Solar Energy*.
231. Yagi, J., Akiyama, T. (1995). Storage of thermal energy for effective use of waste heat from industries. *Journal of Materials Processing Technology* 48: 793 - 804.
232. Yamaha, M., Syuku, K., Misaki, S. (2001). A study on thermal characteristics of thermal storage tank using phase change materials installed in an air distribution system. *Journal of Architectural Planning Environmental Engineering* 549(11): 51–57.
233. Yimmer, B., Adami, M. 1989. Parametric study and optimization of phase change thermal energy storage systems. National Heat Transfer Conference, HTD. Multiphase Flow, Heat, and Mass Transfer 109: 1 - 8.
234. Ying, Bo-An; Kwok, Yi-Lin; Li, Yi; Zhu, Q.Y., Yeung, C.Y. (2004). Assessing the performance of textiles incorporating phase change materials. *polymer testing* 23: 541–549.
235. Zalba, B., Marin J.M., Cabeza, L.F., Mehling, H. (2003). Review on thermal energy storage with phase change: materials, heat transfer analysis and applications. *Applied Thermal Engineering* 23: 251-283.
236. Zhang, J. (1999). Energy saving technology of refrigeration devices. Mechanical Industry Press, Beijing. Zhang, J.J., Zhang, J.L., He, S.M., Wu, K.Z., Liu, X.D. (2001). Thermal studies on the solid-liquid phase transition in binary systems of fatty acids. *Thermochemica Acta* 369: 157-60.
237. Zhang, Y., Jiang, Y. (1999). A simple method, the T-history method, of determining the heat of fusion, specific heat and thermal conductivity of phase-change materials. *Measurement and Sci- ence Technology* 10: 201–

TABLE 1: LIST OF ORGANIC PCMS.

Material	Melting point (°C)	Latent heat (KJ/Kg)	Material	Melting point (°C)	Latent heat (KJ/Kg)
N-Tetradecane	5.5	226	N-Pentacosane	53.7	164
Formic acid	7.8	247	Myristic acid	54.0	199
N-Pentadecane	10.0	205	Oxolate	54.3	178
Acetic acid	16.7	273	Tristearin	54.5	191
N-Hexadecane	16.7	237	O-Xylene dichloride	55.0	121
Caprilone	40.0	260	β Chloroacetic acid	56.0	147
Docasyle bromide	40.0	201	N-Hexacosane	56.3	255
N-Henicosane	40.5	161	Nitro naphthalene	56.7	103
Phenol	41.0	120	α Chloroacetic acid	61.2	130
N-Lauric acid	43.0	183	N-Octacosane	61.4	134
P-Joluidine	43.3	167	Palmitic acid	61.8	164
Cynamide	44.0	209	Bees wax	61.8	177
N-Docosane	44.5	157	Glyolic acid	63.0	109
N-Tricosane	47.6	130	P-Bromophenol	63.5	86
Hydrocinnamic acid	48.0	118	Azobenzene	67.1	121
Cetyl alcohol	49.3	141	Acrylic Acid	68.0	115
O-Nitroaniline	50.0	93	Dintro toluene (2,4)	70.0	111
Camphene	50.0	239	Phenylacetic acid	76.7	102
Diphenyl amine	52.9	107	Thiosinamine	77.0	140
P-Dichlorobenzene	53.1	121	Benzylamine	78.0	174

TABLE 2: LIST OF INORGANIC PCMS.

Material	Melting point (°C)	Latent heat (KJ/Kg)	Material	Melting point (°C)	Latent heat (KJ/Kg)
H ₂ O	0.0	333	BI ₃	31.8	10
POCl ₃	1.0	85	SO ₃ (β)	32.3	151
D ₂ O	3.7	318	TiBr ₄	38.2	23
SbCl ₅	4.0	33	H ₄ P ₂ O ₆	55.0	213
H ₂ SO ₄	10.4	100	SO ₃ (γ)	62.1	331
IC 1 (β)	13.9	56	SbCl ₃	73.4	25
MOF ₆	17.0	50	NaNO ₃	307	199
SO ₃ (α)	17.0	108	KNO ₃	380	266
IC 1 (α)	17.2	69	KOH	380	149
P ₄ O ₆	23.7	64	MgCl ₂	800	492
H ₃ PO ₄	26.0	147	NaCl	802	492
Cs	28.3	15	Na ₂ CO ₃	854	275
Ga	30.0	80	KF	857	452
AsBr ₃	30.0	38	K ₂ CO ₃	897	235
SnBr ₄	30.0	28			

TABLE 3 MELTING POINT AND LATENT HEAT OF FUSION OF PARAFFINS.

Name	No. of "C" Atoms	Melting Point (°C)	Density (kg/m ³)	Thermal Conductivity (W/mK)	Latent Heat (kJ/kg)
n - Dodecane	12	-12	750	0.21 ^S	n.a.
n - Tridecane	13	-6	756		n.a.
n - Tetradecane	14	4.5-5.6	771		231
n - Pentadecane	15	10	768	0.17	207
n - Hexadecane	16	18.2	774	0.21 ^S	238
n - Heptadecane	17	22	778		215
n - Octadecane	18	28.2	814 ^S [14], 775 ^L [14]	0.35 ^S [14], 0.149 ^L [14]	245
n - Nonadecane	19	31.9	912 ^S , 769 ^L	0.21 ^S	222
n - Eicosane	20	37			247
n - Heneicosane	21	41			215
n - Docosane	22	44			249
n - Tricosane	23	47			234
n - Tetracosane	24	51			255
n - Pentacosane	25	54			238
Paraffin wax	n.a.	32	785 ^S [15], 749 ^L [15]	0.514 ^S [15], 0.224 ^L [15]	251[15]
n - Hexacosane	26	56	770	0.21 ^S	257
n - Heptacosane	27	59	773		236
n - Octacosane	28	61	910 ^S , 765 ^L		255
n - Nonacosane	29	64			240
n - Triacontane	30	65			252
n - Hentriacontane	31	n.a.	930 ^S , 830 ^L		n.a.
n - Dotriacontane	32	70			n.a.
n - Tritriacontane	33	71			189

S: solid; L: liquid; n.a.: not available.

Lane, 1983; Abhat, 1983; Garg et al., 1985; Buddhi, 1994; Hale et al., 1971; Sharma, 1999.

Table 4 Melting Point and Latent Heat of Fusion of Non - paraffins.

Name	Melting Point (°C)	Density (kg/m ³)	Latent Heat (kJ/ kg)
Formic acid	7.8	1226.7 ^{15C}	247
Acetic acid	16.7	1050 ^{20C}	187
Glycerin	17.9	1260 ^{20C}	198.7
Lithium chloride ethanolate	21	n.a.	188
Polyethylene glycol 600	20–25	1100 ^{20C}	146
D – Lactic acid	26	1249 ^{15C}	184
1-3 Methyl pentacosane	29	n.a.	197
Camphenilone	39	n.a.	205
Docasyl bromide	40	n.a.	201
Caprylone	40	n.a.	259
Heptadecanone	41	n.a.	201
1-Cyclohexyloctadecane	41	n.a.	218
4-Heptadecanone	41	n.a.	197
Cyanamide	44	1080 ^{20C}	209
Methyl eicosanate	45	851 ^{79C}	230
3-Heptadecanone	48	n.a.	218
2-Heptadecanone	48	n.a.	218
Camphene	50	842 ^{54C}	238
9-Heptadecanone	51	n.a.	213
Methyl behenate	52	n.a.	234
Pentadecanoic acid	52.5	n.a.	178
Hypophosphoric acid	55	n.a.	213
Chloroacetic acid	56	1580 ^{20C}	130
Trimyristin	33–57	862 ^{20C}	201–213
Heptaudecanoic acid	60.6	n.a.	189
Bee wax	61.8	950	177
Glycolic acid	63	n.a.	109
Oxazoline wax-TS 970	74	n.a.	Arachic acid
76.5	n.a.	227	Bromcamphor
77	1449 ^{81C}	174	Durene
79.3	838 ^{20C}	156	Acetamide
81	1159	241	Methyl brombrenzoate
81	n.a.	126	Alpha naphthol
96	1095 ^{98.7C}	163	Glutaric acid
97.5	1429	156	p-Xylene dichloride
100	n.a.	138.7	
Methyl Fumarate	102	1045	242
Catechol	104.3	1370 ^{15C}	207
Quinone	115	1318 ^{20C}	171
Acetanilide	115	1210 ^{4C}	142
Succinic anhydride	119	1104	204
Benzoic acid	121.7	1266 ^{15C}	142.8
Stibene	124	1164 ^{15C}	167
Benzamide	127.2	1341	169.4
Phenacetin	137	n.a.	136.7
Alpha glucose	141	1544	174
Acetyl – p- toluidene	146	n.a.	180
Phenylhdrazone benzaldehyde	155	n.a.	134.8
Salicylic acid	159	1443 ^{20C}	199
Benzanilide	161	n.a.	162
O-Mannitol	166	1489 ^{20C}	294
Hydroquinone	172.4	1358 ^{20C}	258
p-Aminobenzoic acid	187	n.a.	153

Table 5 Melting Point and Latent Heat of Fusion of Fatty Acids.

Name	Melting Point (°C)	Density (kg/m ³) (W/mK)	Thermal Conductivity	Latent Heat (kJ/kg)
Propyl palmitate	10	n.a.	n.a.	186
Isopropyl palmitate	11	n.a.	n.a.	100
Oleic acid	13.5-16.3	863 ^{60C}	n.a.	n.a.
Isopropyl stearate	14-19	n.a.	n.a.	140-142
Caprylic acid	16 16.3	901 ^{30C} 862 ^{80C} 981 ^{13C} 1033 ^{10C}	0.149 ^{39C} 0.145 ^{67.7C} , 0.148 ^{20C}	148 149
Butyl stearate	19	n.a.	n.a.	140 123-200
Dimethyl sabacate	21	n.a.	n.a.	120-135
Vinyl stearate	27-29	n.a.	n.a.	122
Methyl palmitate	29	n.a.	n.a.	205
Capric acid	32 31.5	878 ^{45C} 886 ^{40C} , 1004 ^{24C}	0.153 ^{38.5C} 0.152 ^{55.5C} , 0.149 ^{40C}	152.7 153
Erucic acid	33	853 ^{70C}	n.a.	n.a.
Methyl-12-hydroxy-stearate	42-43	n.a.	n.a.	120-126
Lauric acid	42-44	862 ^{60C} , 1007 ^{24C}	n.a.	178
Elaidic acid	47	851 ^{79C}	n.a.	218
Pelargonic acid	48	n.a.	n.a.	n.a.
Myristic acid	49-51 54	861 ^{55C} 844 ^{80C}	n.a. 187	205
Palmitic acid	64 61	850 ^{65C} 847 ^{80C}	0.162 ^{68.4C} 0.159 ^{80.1C}	185.4 203.4
Stearic acid	69 60-61	848 ^{70C} 965 ^{24C}	0.172 ^{70C}	202.5 186.5
Valporic acid	120	n.a.	n.a.	n.a.

Lane, 1983; Abhat, 1983; Garg et al., 1985; Buddhi, 1994; Hale et al., 1971; Sharma, 1999.

Table 6 Melting point and latent heat of fusion of salt hydrates.

Melting Point (°C)		Density (kg/m ³)	Thermal Conductivity (W/m K)	Latent Heat (kJ/kg)	Melting Behavior ^a [13]
LiClO ₃ .3H ₂ O	8	n.a.	n.a.	253	c
NH ₄ Cl.Na ₂ SO ₄ .10H ₂ O	11	n.a.	n.a.	163	n.a.
K ₂ HO ₄ .6H ₂ O	14	n.a.	n.a.	108	c
NaCl.Na ₂ SO ₄ .10H ₂ O	18	n.a.	n.a.	286	n.a.
KF.4H ₂ O	18	n.a.	n.a.	330	c
K ₂ HO ₄ .4H ₂ O	18.5	1447 ²⁰ C, 1455 ¹⁸ C, 1480 ⁶ C	n.a.	231	n.a.
Mn(NO ₃) ₂ .6H ₂ O	25 25.8	1738 ²⁰ C _[12] , 1728 ⁴⁰ C _[12] , 1795 ⁵ C _[12]	n.a. 125.9[12]	148	n.a.
LiBO ₂ .8H ₂ O	25.7	n.a.	n.a.	289	n.a.
FeBr ₃ .6H ₂ O	27	n.a.	n.a.	105	n.a.
CaCl ₂ .6H ₂ O	29–30	1562 ³² C, 1802 ²⁴ C	0.561 ^{61.2} C, 1.008 ²³ C	170–192	ic
LiNO ₃ .3H ₂ O	30	n.a.	n.a.	189–296	c
Na ₂ SO ₄ .10H ₂ O	32	1485 ²⁴ C	0.544	251–254	ic
Na ₂ CO ₃ .10H ₂ O	33–36	1442	n.a.	247	ic
KFe(SO ₄) ₂ .12H ₂ O	33	n.a.	n.a.	173	ic
CaBr ₂ .6H ₂ O	34	1956 ³⁵ C, 2194 ²⁴ C	n.a.	115–138	n.a.
LiBr.2H ₂ O	34	n.a.	n.a.	124	ic
Na ₂ HPO ₄ .12H ₂ O	35	1522	n.a.	256–281	ic
Zn(NO ₃) ₂ .6H ₂ O	36	1828 ³⁶ C, 1937 ²⁴ C, 2065 ¹⁴ C	0.464 ^{39.9} C, 0.469 ^{61.2} C	134–147	c
Mn(NO ₃) ₂ .4H ₂ O	37	n.a.	n.a.	115	n.a.
FeCl ₃ .6H ₂ O	37	n.a.	n.a.	223	c
CaCl ₂ .4H ₂ O	39	n.a.	n.a.	158	ic
CoSO ₄ .7H ₂ O	40.7	n.a.	n.a.	170	n.a.
CuSO ₄ .7H ₂ O	40.7	n.a.	n.a.	171	n.a.
KF.2H ₂ O	42	n.a.	n.a.	162–266	c
MgI ₂ .8H ₂ O	42	n.a.	n.a.	133	n.a.
CaI ₂ .6H ₂ O	42	n.a.	n.a.	162	n.a.
Ca(NO ₃) ₂ .4H ₂ O	43–47	n.a.	n.a.	106–140	c
Zn(NO ₃) ₂ .4H ₂ O	45	n.a.	n.a.	110	n.a.
K ₃ PO ₄ .7H ₂ O	45	n.a.	n.a.	145	n.a.
Fe(NO ₃) ₃ .9H ₂ O	47	n.a.	n.a.	155–190	ic
Mg(NO ₃) ₃ .4H ₂ O	47	n.a.	n.a.	142	n.a.
Na ₂ SiO ₃ .5H ₂ O	48	n.a.	n.a.	168	n.a.
Na ₂ HPO ₄ .7H ₂ O	48	n.a.	n.a.	135–170	ic
Na ₂ S ₂ O ₃ .5H ₂ O	48	1600	n.a.	209	n.a.
K ₂ HPO ₄ .3H ₂ O	48	n.a.	n.a.	99	n.a.
MgSO ₄ .7H ₂ O	48.4	n.a.	n.a.	202	n.a.
Ca(NO ₃) ₂ .3H ₂ O	51	n.a.	n.a.	104	n.a.
Na(NO ₃) ₂ .6H ₂ O	53	n.a.	n.a.	158	n.a.
Zn(NO ₃) ₂ .2H ₂ O	55	n.a.	n.a.	68	c
FeCl ₃ .2H ₂ O	56	n.a.	n.a.	90	n.a.
CO(NO ₃) ₂ .6H ₂ O	57	n.a.	n.a.	115	n.a.
Ni(NO ₃) ₂ .6H ₂ O	57	n.a.	n.a.	168	n.a.

MnCl ₂ .4H ₂ O	58	n.a.	n.a.	151	n.a.
CH ₃ COONa.3H ₂ O	58	n.a.	n.a.	270–290	ic
LiC ₂ H ₃ O ₂ .2H ₂ O	58	n.a.	n.a.	251–377	n.a.
MgCl ₂ .4H ₂ O	58.0	n.a.	n.a.	178	n.a.
NaOH.H ₂ O	58	n.a.	n.a.	272	n.a.
Na(CH ₃ COO).3H ₂ O	58	n.a.	n.a.	n.a.	n.a.
Cd(NO ₃) ₂ .4H ₂ O	59	n.a.	n.a.	98	n.a.
Cd(NO ₃) ₂ .1H ₂ O	59.5	n.a.	n.a.	107	n.a.
Fe(NO ₃) ₂ .6H ₂ O	60	n.a.	n.a.	125	n.a.
NaAl(SO ₄) ₂ .12H ₂ O	61	n.a.	n.a.	181	ic
FeSO ₄ .7H ₂ O	64	n.a.	n.a.	200	n.a.
Na ₃ PO ₄ .12H ₂ O	65	n.a.	n.a.	168	n.a.
Na ₂ B ₄ O ₇ .10H ₂ O	68	n.a.	n.a.	n.a.	n.a.
Na ₃ PO ₄ .12H ₂ O	69	n.a.	n.a.	n.a.	n.a.
LiCH ₃ COO.2H ₂ O	70	n.a.	n.a.	150–251	c
Na ₂ P ₂ O ₇ .10H ₂ O	70	n.a.	n.a.	186–230	ic
Al(NO ₃) ₂ .9H ₂ O	72	n.a.	n.a.	155–176	ic
Ba(OH) ₂ .8H ₂ O	78	1937 ^{84C} , 2070 ^{24C} , 2180	0.653 ^{85.7C} , 0.678 ^{98.2C} , 1.255 ^{23C}	265–280	c
Al ₂ (SO ₄) ₃ .18H ₂ O	88	n.a.	n.a.	218	ic
Sr(OH) ₂ .8H ₂ O	89	n.a.	n.a.	370	ic
Mg(NO ₃) ₂ .6H ₂ O	89–90	1550 ^{94C} , 1636 ^{25C}	0.490 ^{95C} , 0.502 ^{110C} , 0.611 ^{37C} , 0.669 ^{55.6C}	162–167	c
KAl(SO ₄) ₂ .12H ₂ O	91	n.a.	n.a.	184	n.a.
(NH ₄)Al(SO ₄).6H ₂ O	95	n.a.	n.a.	269	n.a.
Na ₂ S.51/2H ₂ O	97.5	n.a.	n.a.	n.a.	n.a.
LiCl.H ₂ O	99	n.a.	n.a.	212	ic
CaBr ₂ .4H ₂ O	110	n.a.	n.a.	n.a.	n.a.
Al ₂ (SO ₄) ₂ .16H ₂ O	112	n.a.	n.a.	n.a.	n.a.
MgCl ₂ . 6H ₂ O	115–117	1450 ^{120C} , 1442 ^{78C} , 1569 ^{20C} , 1570 ^{20C}	0.570 ^{120C} , 0.598 ^{140C} , 0.694 ^{90C} , 0.704 ^{110C}	165–169	n.a.
NaC ₂ H ₃ O ₂ .3H ₂ O	137	1450	n.a.	172	n.a.

n.a.: not available; c: congruent melting; ic: incongruent melting.
Lane, 1983; Abhat, 1983; Garg et al., 1985; Buddhi, 1994; Hale et al., 1971; Sharma, 1999.

Table 7 List of Organic and Inorganic Eutectics.

Name	Composition (wt %)	Melting Point (°C)	Latent Heat (kJ/ kg)
Na ₂ SO ₄ +NaCl+KCl+H ₂ O	31+13+16+40	4	234
Na ₂ SO ₄ +NaCl+NH ₄ Cl+H ₂ O	32+14+12+42	11	n.a.
C ₅ H ₅ C ₆ H ₅ + (C ₆ H ₅) ₂ O	26.5+73.5	12	97.9
Na ₂ SO ₄ +NaCl+H ₂ O	37+17+46	18	n.a.
Na ₂ S ₄ +MgSO ₄ +H ₂ O	25+21+54	24	n.a.
C ₁₄ H ₂₈ O ₂ +C ₁₀ H ₂₀ O ₂	34+66	24	147.7
Ca(NO ₃) ₃ .4H ₂ O+Mg(NO ₃) ₃ .6H ₂ O	47+53	30	136
NH ₂ CONH ₂ +NH ₄ NO ₃	–	46	95
Mg(NO ₃) ₂ .6H ₂ O+NH ₄ NO ₃	61.5+38.4	52	125.5
Mg(NO ₃) ₂ .6H ₂ O+MgCl ₂ .6H ₂ O	58.7+41.3	59	132.2
Mg(NO ₃) ₂ .6H ₂ O+Al(NO ₃) ₂ .9H ₂ O	53+47	61	148
Mg(NO ₃) ₂ .6H ₂ O+MgBr ₂ .6H ₂ O	59+41	66	168
Napthalene + Benzoic Acid	67.1+32.9	67	123.4
AlCl ₃ +NaCl+ZrCl ₂	79+17+4	68	234
AlCl ₃ +NaCl+KCl	66+20+14	70	209
NH ₂ CONH ₂ +NH ₄ Br	66.6+33.4	76	151
LiNO ₃ + NH ₄ NO ₃ +NaNO ₃	25+65+10	80.5	113
AlCl ₃ +NaCl+KCl	60+26+14	93	213
AlCl ₃ +NaCl	66+34	93	201
NaNO ₂ +NaNO ₃ +KNO ₃	40+7+53	142	n.a.

a.: not available.
Lane, 1983; Abhat, 1983; Garg et al., 1985; Buddhi, 1994; Hale et al., 1971; Sharma, 1999.

Table 8 Melting Point and Latent Heat of Fusion of Some Selected Solid - Solid PCMs.

Name	Melting Point (°C)	Latent Heat (kJ/kg)
38.2%NPG/61.8%PE	26–32	18–75
38.2%NPG/61.8%TAM	22–35	27–33
76.4%NPG/33.6%TAM	28–38	75–80
76.4%NPG/33.6%PE	31–37	35–46
91%NPG/9%PE	31–36	68
91%NPG/9%TAM	30–39	143–150
Neopentyl glycol (NPG)	43	130
Diamnorpentacrythritol	68	184
2-Amino - 2 - methyl - 1, 3 - propanediol	78	264
2 - Methyl - 2 - mtro - 1, 3 - propanediol	79	201
Trumethylolethane	81	192
Pentaglycerin	81	192
2-Hydroxymethyl-2-methyl-1, 3 – propanediol	81	192
Monoaminopentaerythritol	86	192
Cross-linked polyethylene	110–115	125–146
Tris(Hydroxymethyl)acetic acid	124	205
2-Amino-2-hydroxymethyl-1, 3 – propanediol	131	285
Cross-linked HDPE	125–146	167–201
2,2-Bis(Hydroxymethyl) Propionic acid	152	289
38.2%NPG/61.8%PE	170	147
Penterythritol (PE)	185	303

Lane, 1983; Abhat, 1983; Garg et al., 1985; Buddhi, 1994; Hale et al., 1971; Sharma, 1999.

Table 9 List of Commercially Available PCMs (0 °C–118 °C).

Name	Melting Point (°C)	Latent Heat (kJ/kg)	Density (kg/m ³)	Manufacturer
TH 0	0	334	n.a.	TEAP (www.teappcm.com)
A 4	4	227	766	EPS Ltd. (www.eps Ltd.co.uk)
Witco 85010-1	4	129.6	n.a.	Witco
RT 2	6	156	860	Rubitherm (www.rubitherm.com)
TH 7	7	189	n.a.	TEAP (www.teappcm.com)
RT 5	7	156	860	Rubitherm (www.rubitherm.com)
E 7	7	120	1540	EPS Ltd. (www.eps Ltd.co.uk)
C 7	7	162	1420	Climator (www.climator.com)
RT 6	8	174	860	Rubitherm (www.rubitherm.com)
E 8	8	140	1470	EPS Ltd. (www.eps Ltd.co.uk)
A 8	8	220	770	EPS Ltd. (www.eps Ltd.co.uk)
E 10	10	140	1520	EPS Ltd. (www.eps Ltd.co.uk)
E 13	13	140	1780	EPS Ltd. (www.eps Ltd.co.uk)
C 15	15	130	n.a.	Climator (www.climator.com)
E 21	21	150	1480	EPS Ltd. (www.eps Ltd.co.uk)
RT 20	22	172	870	Rubitherm (www.rubitherm.com)
A 22	22	220	770	EPS Ltd. (www.eps Ltd.co.uk)
C 24	24	216	1480	Climator (www.climator.com)
RT 26	25	131	880	Rubitherm (www.rubitherm.com)
TH 25	25	159	n.a.	TEAP (www.teappcm.com)
Witco 45 A	26.3	167.2	n.a.	Witco
S 27	27	207	1470	Cristopia (www.cristopia.com)
STL 27	27	213	1090	Mitsubishi Chemical
RT 27	28	179	870	Rubitherm (www.rubitherm.com)
GR 27	28	72	750	Rubitherm (www.rubitherm.com)
PX 27	28	112	640	Rubitherm (www.rubitherm.com)
A 28	28	245	790	EPS Ltd. (www.eps Ltd.co.uk)
TH 29	29	188	1540	TEAP (www.teappcm.com)
E 30	30	201	1300	EPS Ltd. (www.eps Ltd.co.uk)
C 32	32	302	1450	Climator (www.climator.com)
E 32	32	186	1460	EPS Ltd. (www.eps Ltd.co.uk)
RT 35	35	157	880	Rubitherm (www.rubitherm.com)
RT 42	43	174	880	Rubitherm (www.rubitherm.com)
GR 41	43	63	750	Rubitherm (www.rubitherm.com)
FB 41	43	117	750	Rubitherm (www.rubitherm.com)
RT 41	43	152	880	Rubitherm (www.rubitherm.com)
STL 47	47	221	1340	Mitsubishi Chemical
E 48	48	201	1670	EPS Ltd. (www.eps Ltd.co.uk)
C 48	48	324	1360	Climator (www.climator.com)
STL 52	52	201	1300	Mitsubishi Chemical
PX 52	53	103	640	Rubitherm (www.rubitherm.com)
STL 55	55	242	1290	Mitsubishi Chemical
FB 54	55	135	750	Rubitherm (www.rubitherm.com)
RT 54	55	179	900	Rubitherm (www.rubitherm.com)
E 58	58	226	1280	EPS Ltd. (www.eps Ltd.co.uk)
C 58	58	364	1460	Climator (www.climator.com)
TH 58	58	226	1290	TEAP (www.teappcm.com)
RT 65	64	173	910	Rubitherm (www.rubitherm.com)
C 70	70	194	1700	Climator (www.climator.com)
PX 80	77	91	640	Rubitherm (www.rubitherm.com)
GR 80	79	71	750	Rubitherm (www.rubitherm.com)
FB 80	79	132	750	Rubitherm (www.rubitherm.com)
RT 80	79	175	920	Rubitherm (www.rubitherm.com)
PCM 80	80	231	n.a.	Mitsubishi Chemical
PCM 86	86	246	n.a.	Mitsubishi Chemical
E 89	89	163	n.a.	EPS Ltd. (www.eps Ltd.co.uk)
TH 89	89	149	n.a.	TEAP (www.teappcm.com)
RT 90	90	194	930	Rubitherm (www.rubitherm.com)
RT 100	99	168	940	Rubitherm (www.rubitherm.com)
RT 112	112	213	n.a.	Rubitherm (www.rubitherm.com)
E 117	117	169	1450	EPS Ltd. (www.eps Ltd.co.uk)
?	118	339.8	1480	Mitsubishi Chemical